




Structure Tests, Results and Program



- Introduction
- 30 GHz results and test facilities
- 11.4 GHz results and test facilities
- Future testing program
- Conclusion

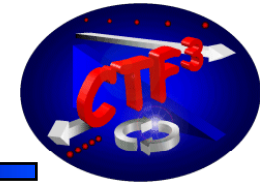

Cosmological Evolution of CLIC



<1994	80 MV/m	single bunch (10 ns)	30 GHz
↕	100 MV/m	multi bunch (130 ns)	30 GHz
1999	150 MV/m	multi bunch (130 ns)	30 GHz
2007	100 MV/m	multi bunch (300 ns)	12 GHz

Time:

Start

Early

Past

Today

Future

Cosmos:

Big Bang

Inflation

Deceleration

Acceleration

Not collapsing

CLIC:

an idea was born

Inflation of Parameters


Problems discovered

New optimism


...



30 GHz results and test facilities

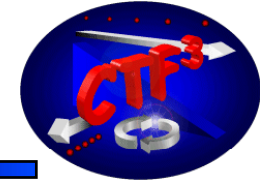

CTF II the two beam test facility

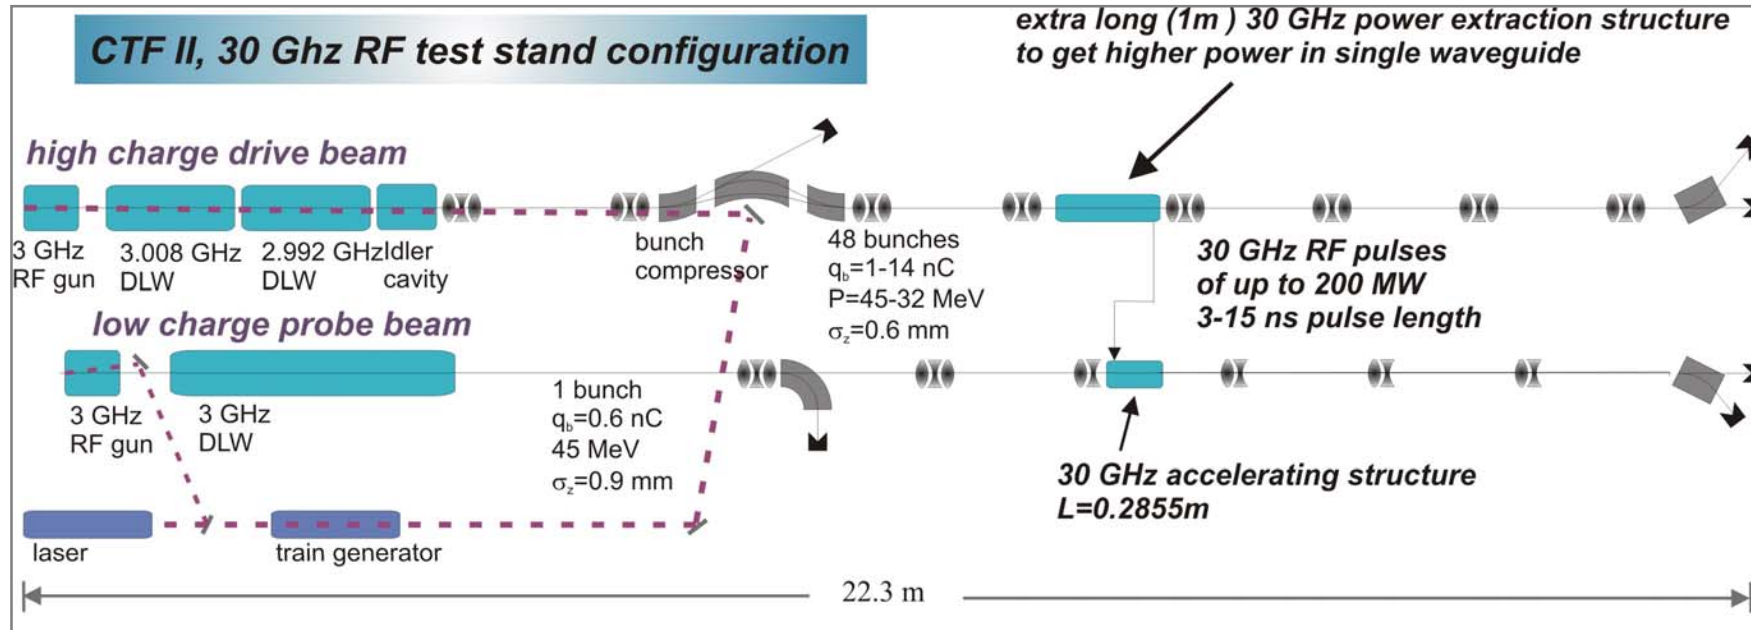

Two Beam Test stand in CTF II:


Up to 300 MW, 16 ns

Successful acceleration in 5 modules

at moderate gradient





30 GHz Power Production

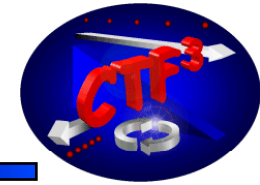

PETS = Power Extraction Structure


CTFII PETS, 300 MW peak power, 16 ns

CLIC PETS
140 MW, 300 ns

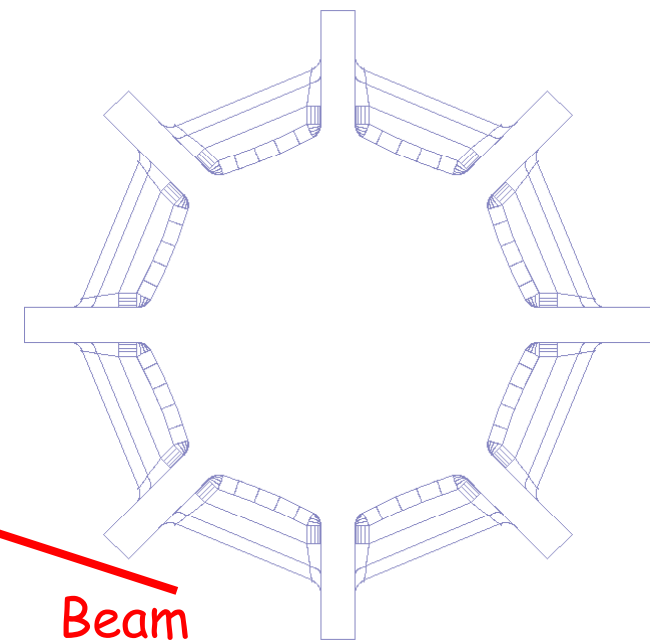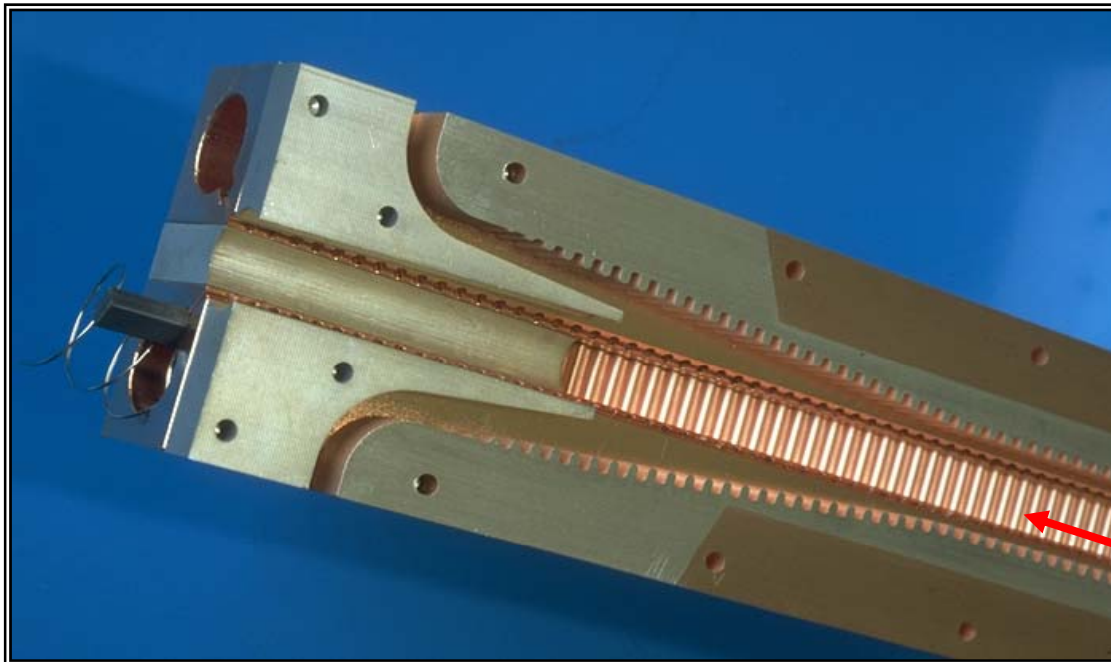






The beginning of a long story, Damage in high field areas

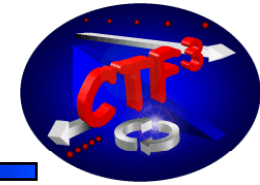

In 1999, damage was found in high field areas of the first CLIC prototype accelerating structures at a gradient $\sim 60\text{-}70\text{ MV/m}$
(Surface field on Copper $\sim 300\text{ MV/m}$)

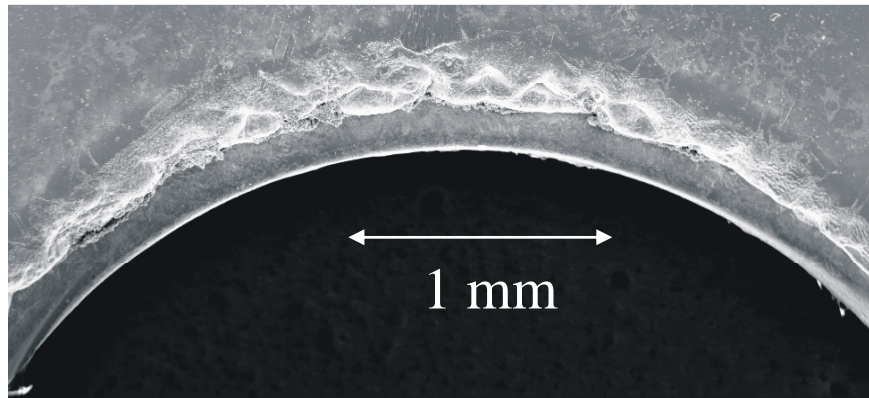

Power
Input
↓

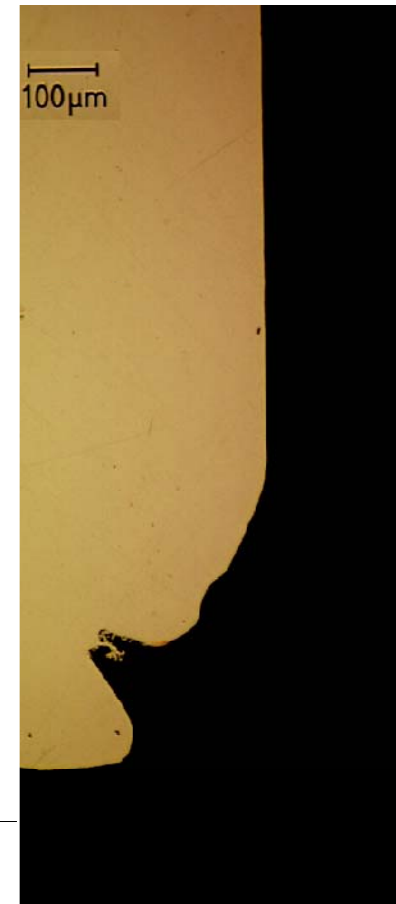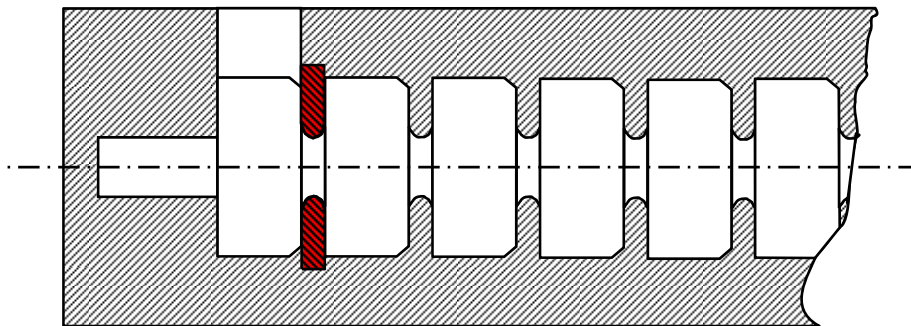





Clamped-Iris Structure Tests in CTF II





Damage in high field areas

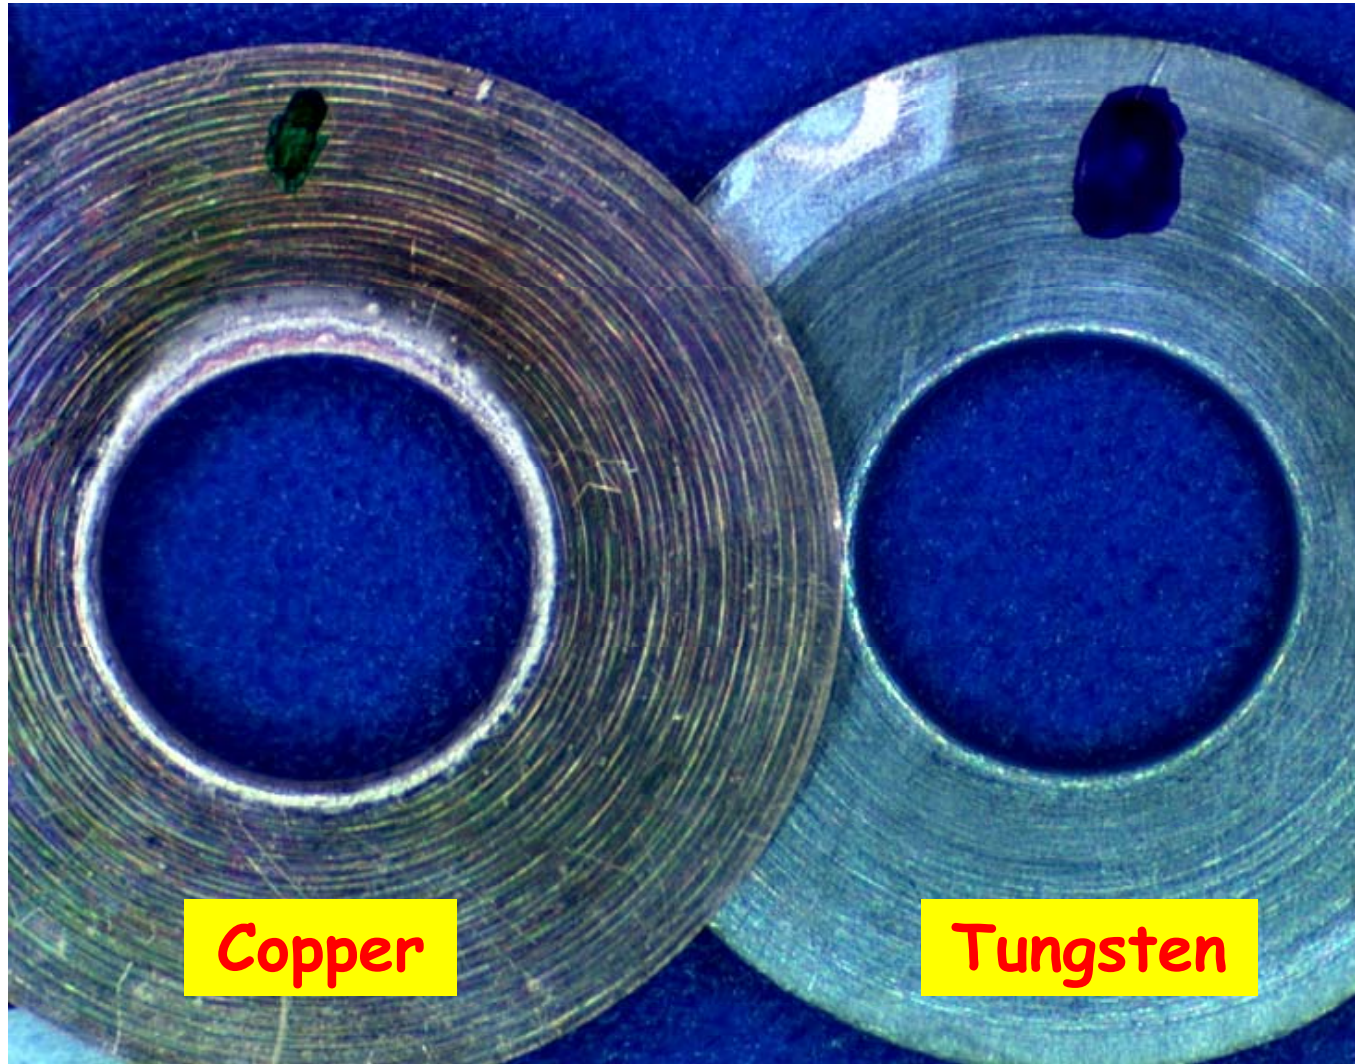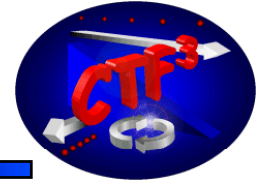

Copper


Tungsten



Accelerating Structure Tests in CTF II




Short, 16 ns rf pulses

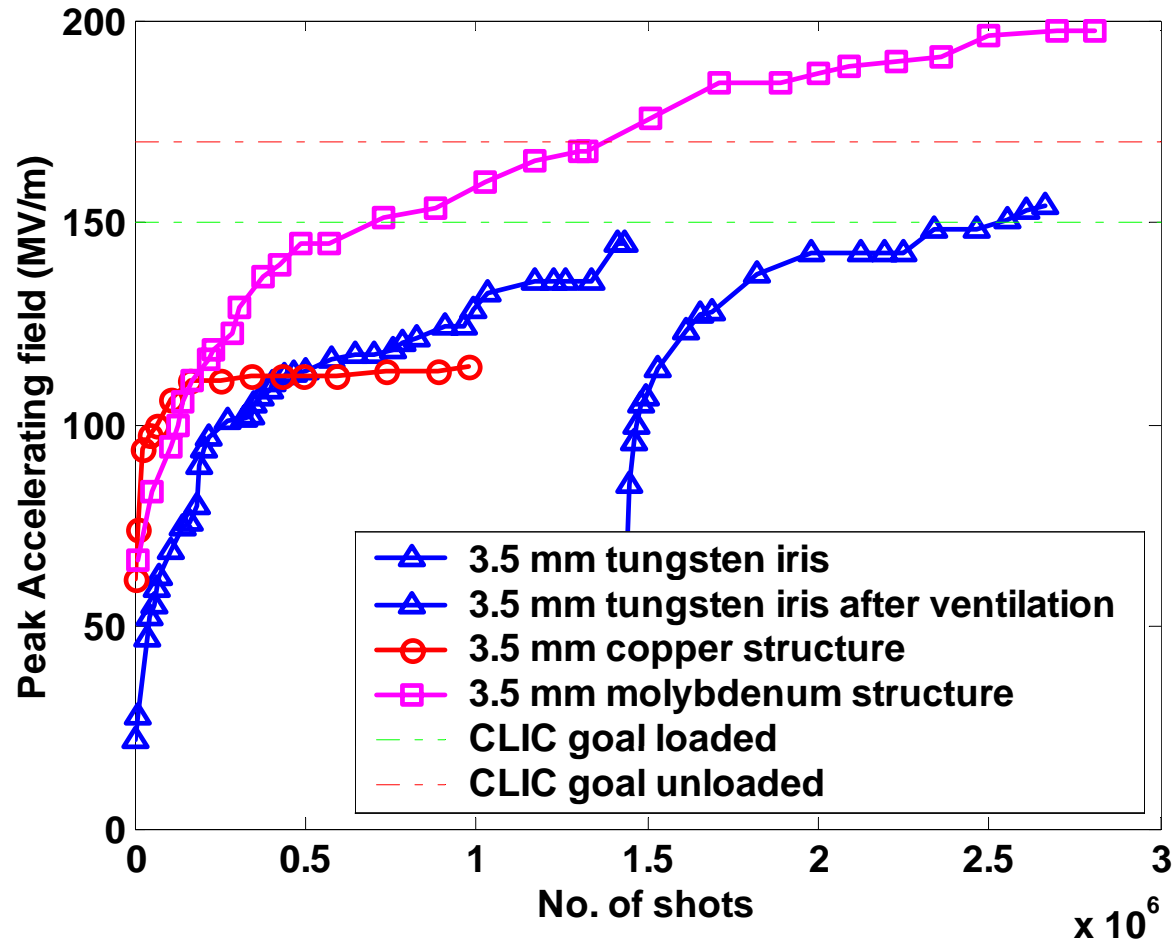

New Record for classical accelerating structures !



Accelerating Structure Tests in CTF II



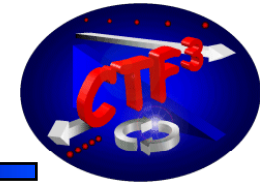


Surface field on first iris

Copper 260 MV/m


Tungsten 340 MV/m

Molybdenum 426 MV/m

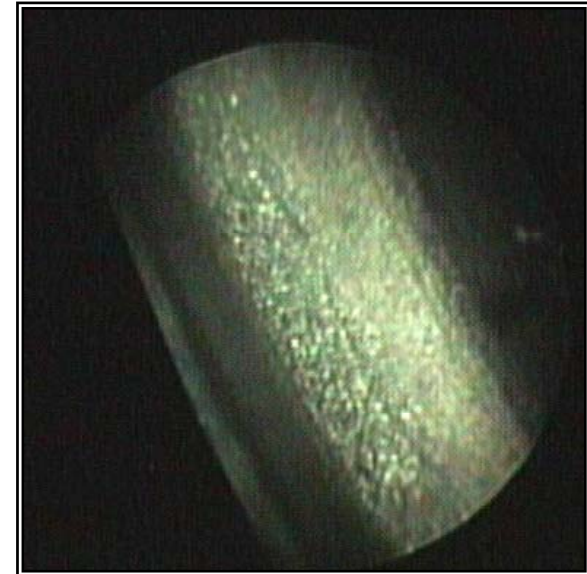
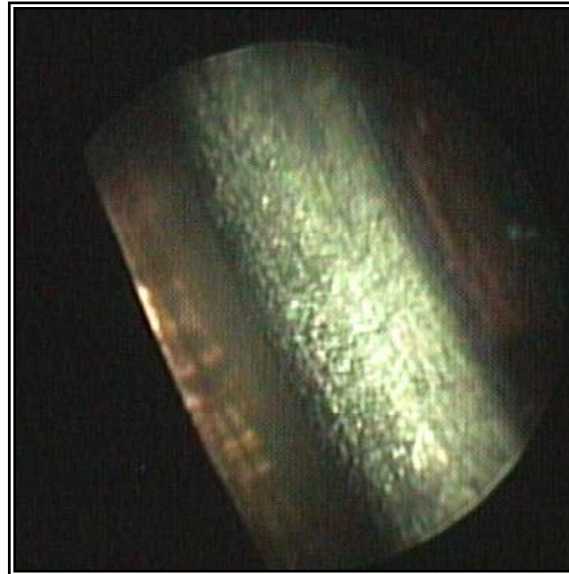
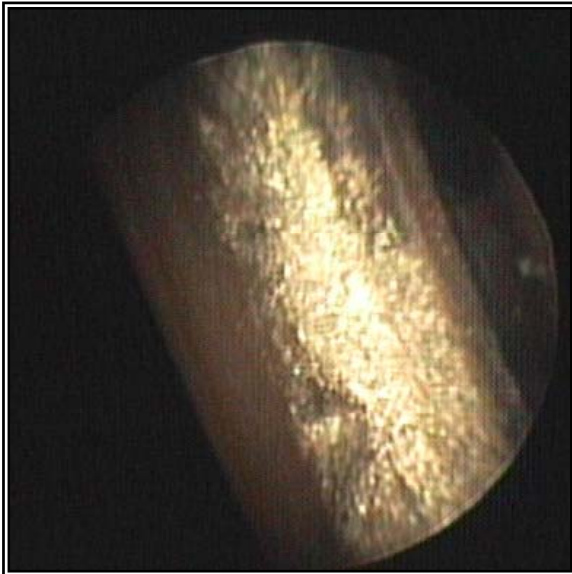




Tapered Damped Structure Test in ASSET

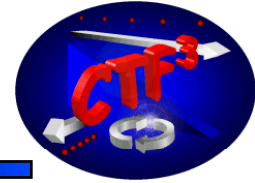


Successful experimental verification of strong cell damping and benchmarking of codes

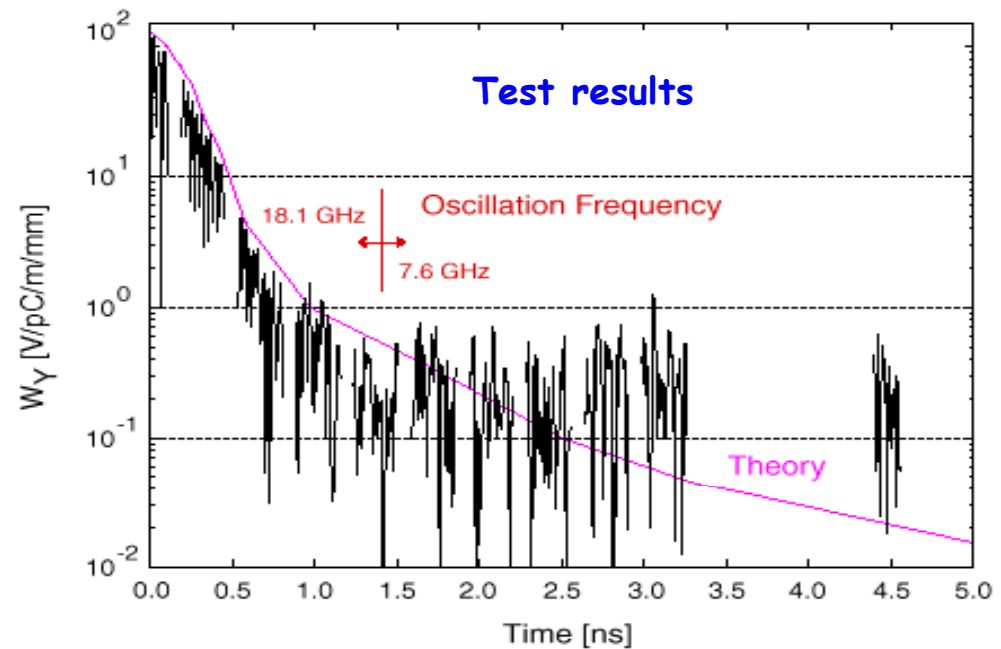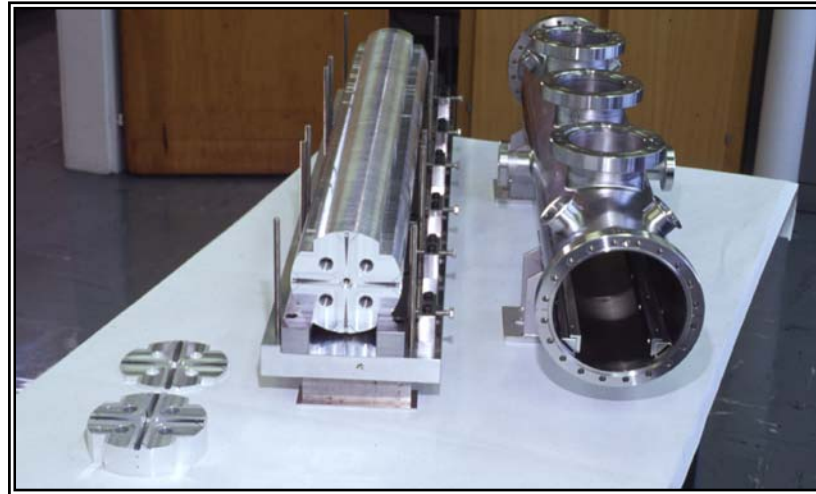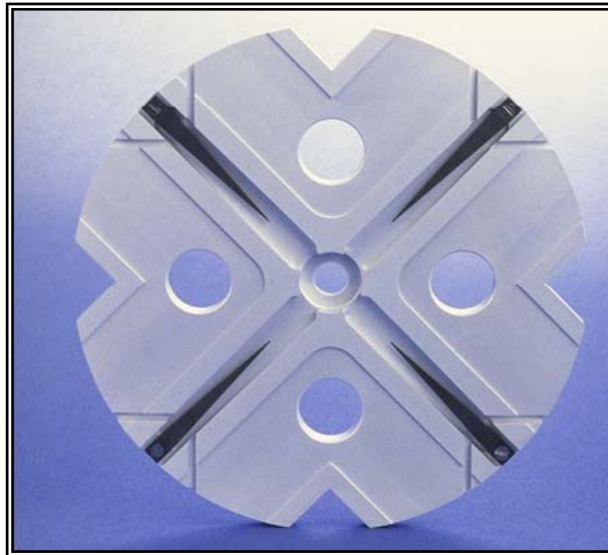




CTF3, towards a CLIC-type drive beam




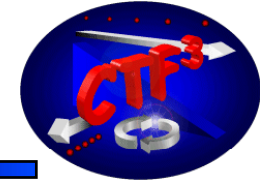


Rf power production with CTF3

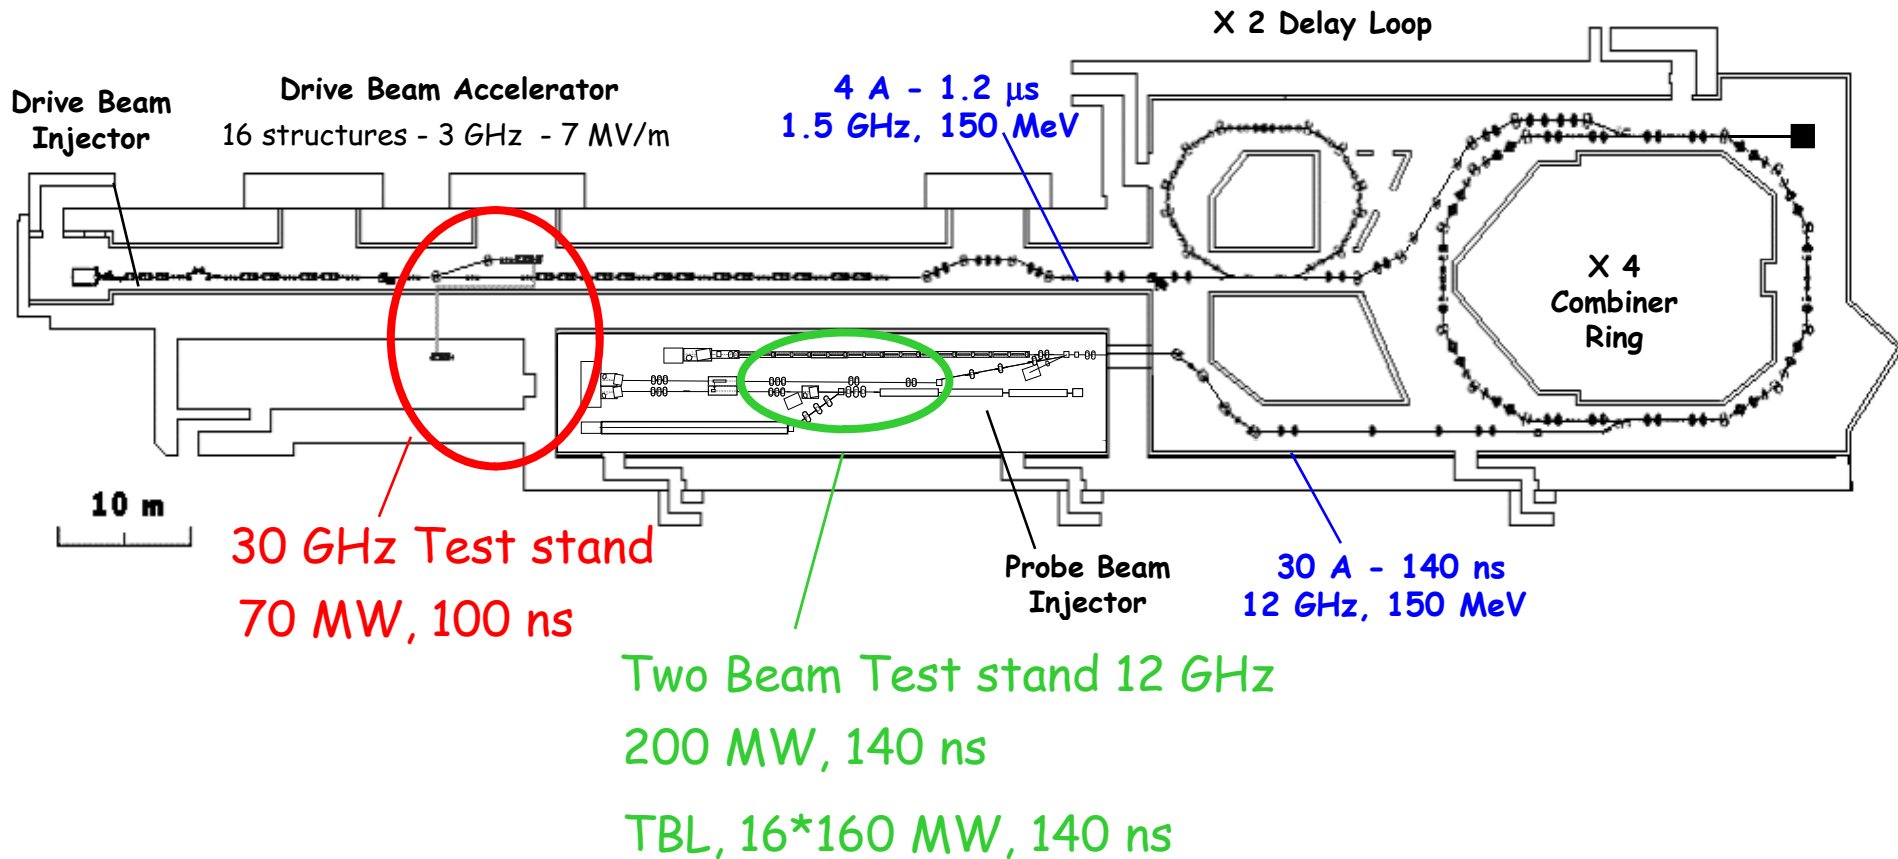






30 GHz Power Production in CTF3

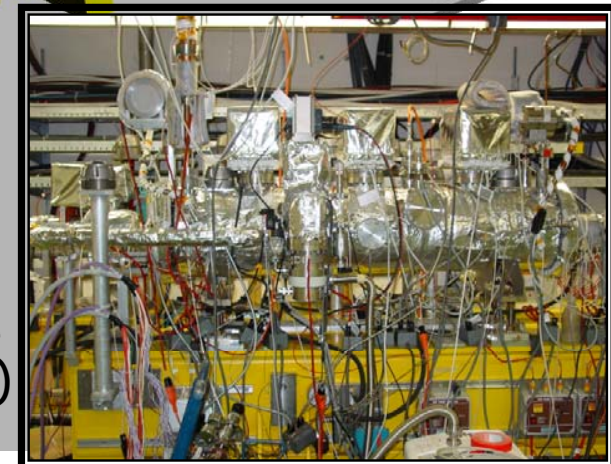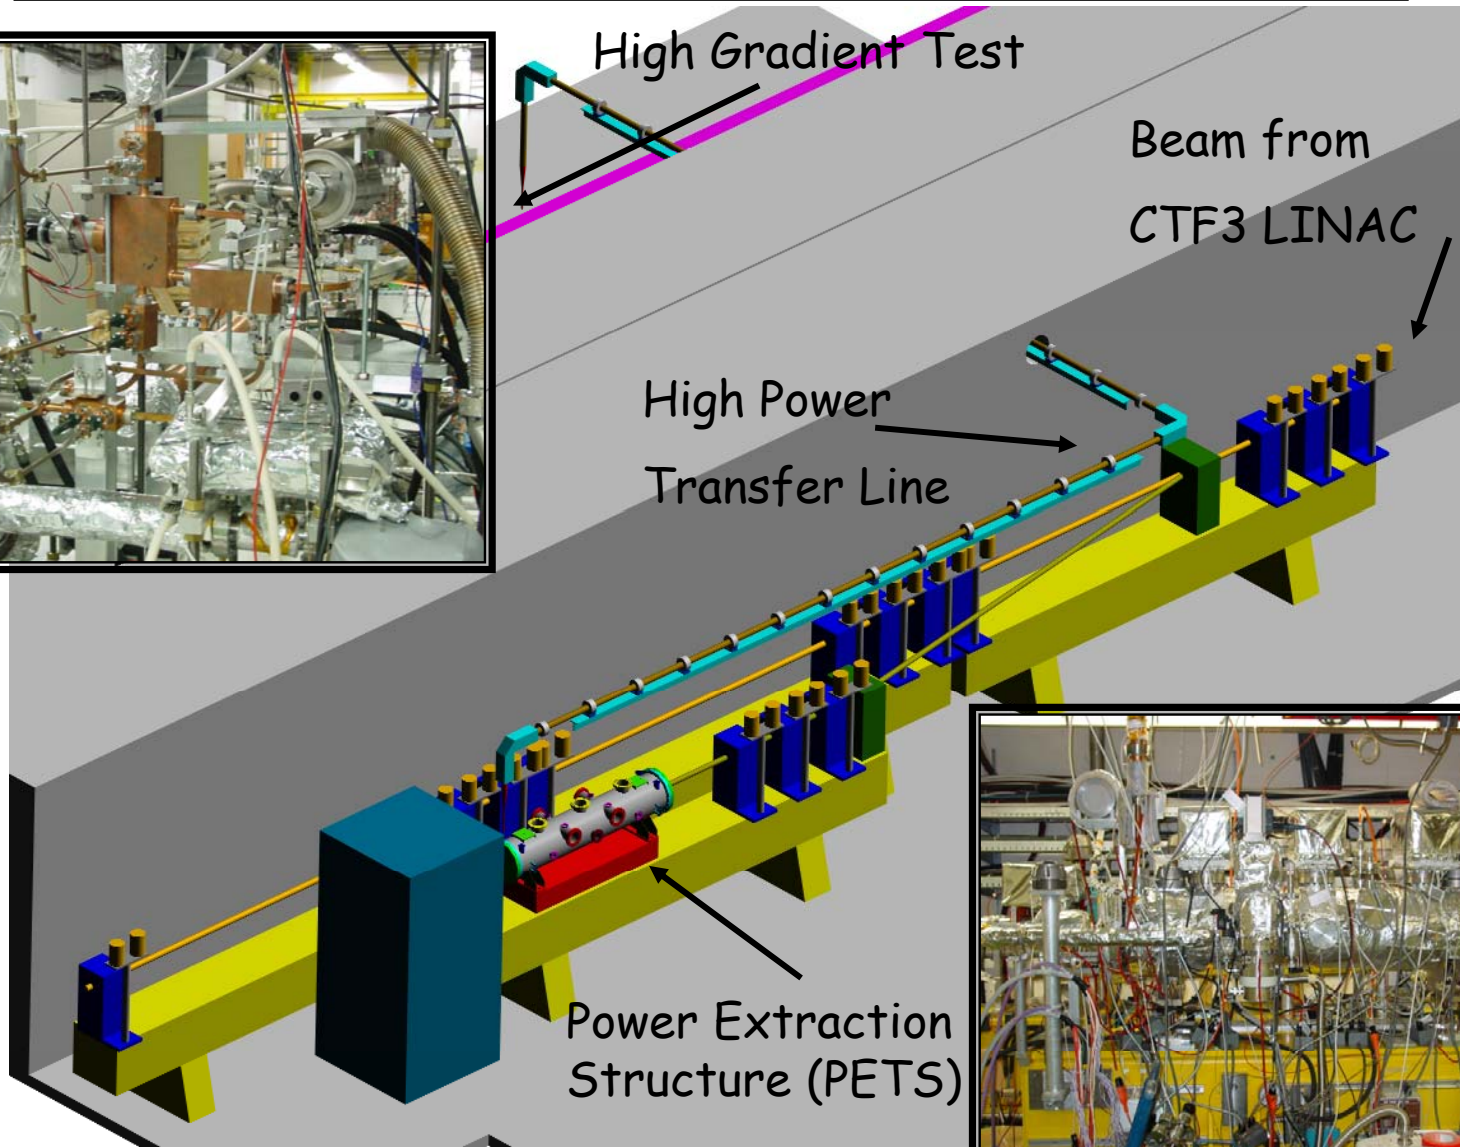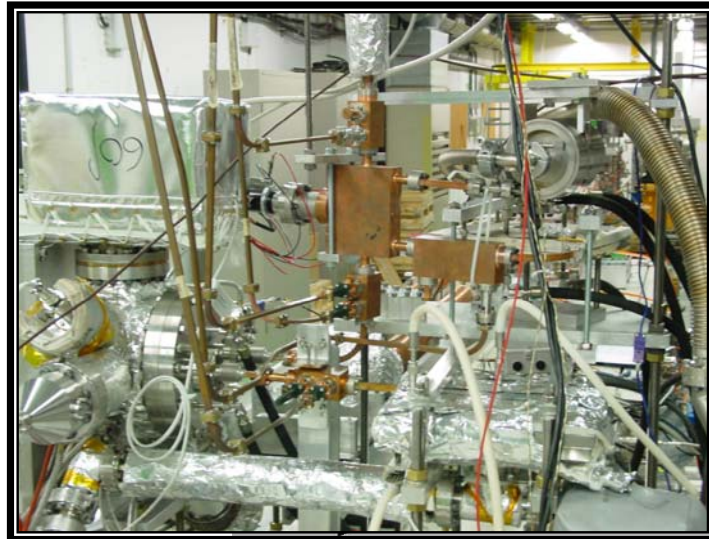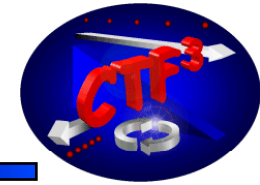





Hybrid Damped Structure (HDS)

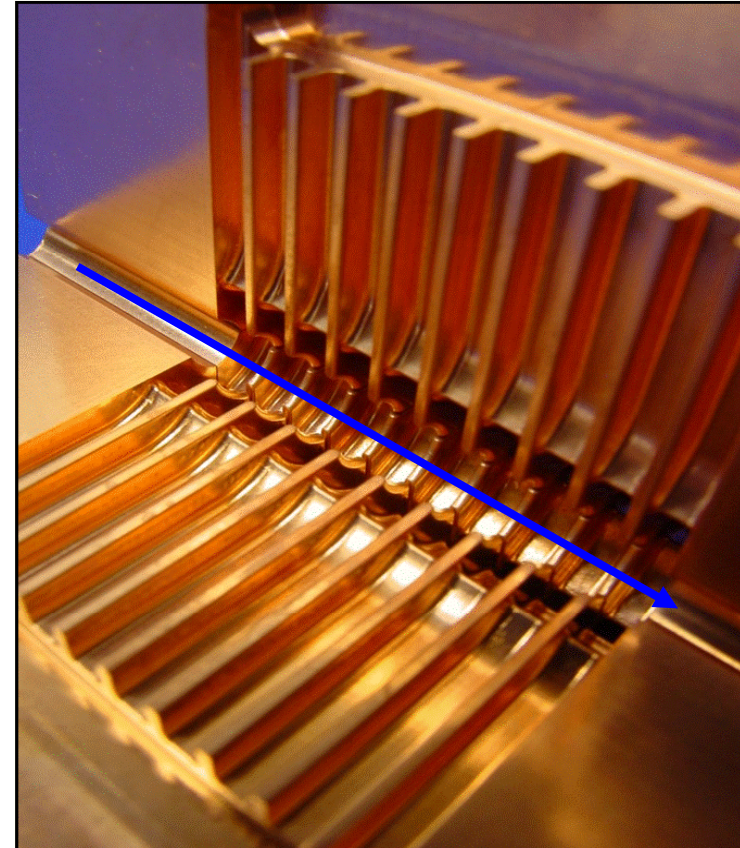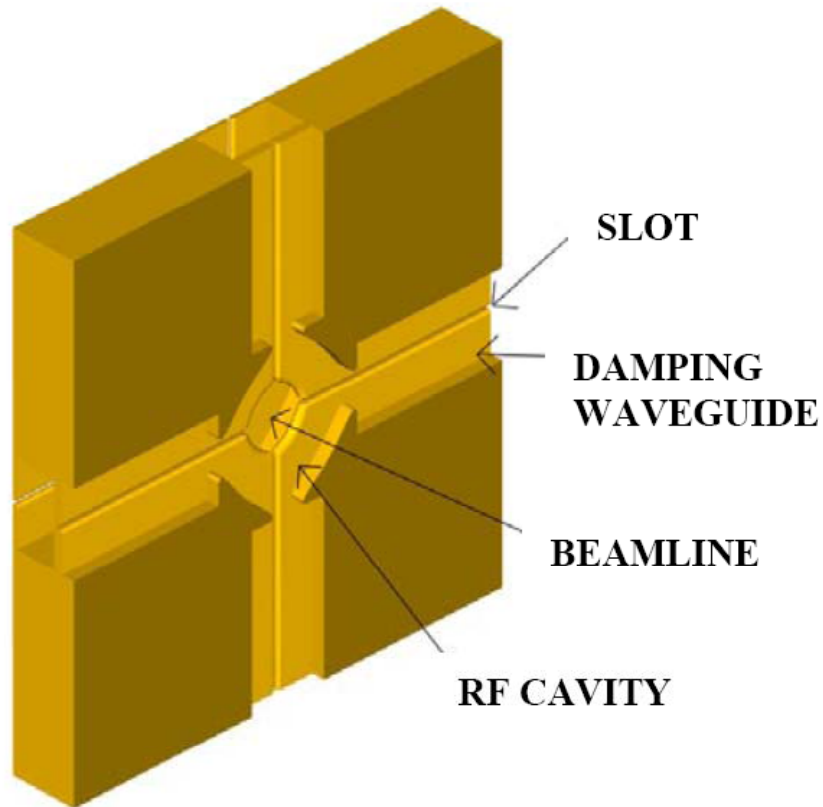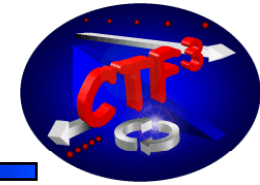

CLIC damped and detuned accelerating structure:
30 GHz, 150 MV/m, 70 ns, $< 10^{-6}$ trip probability



Accelerating Structures made out of milled quadrants

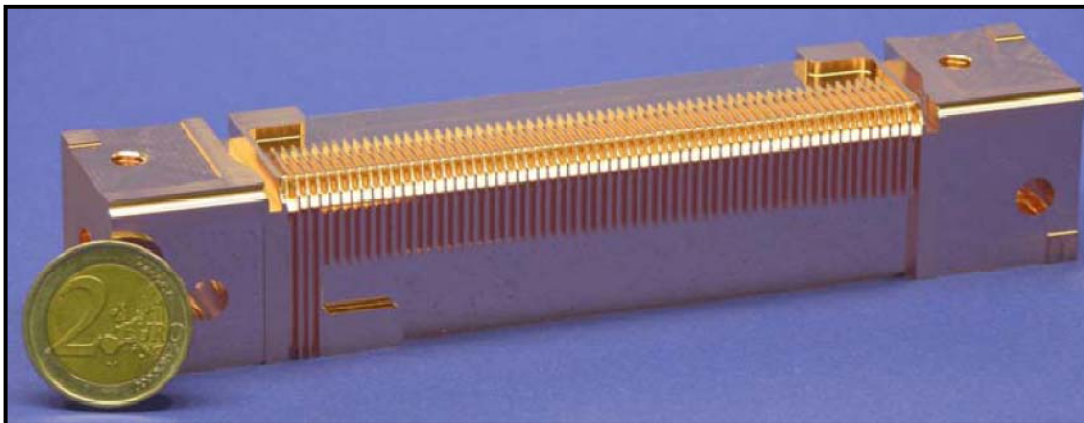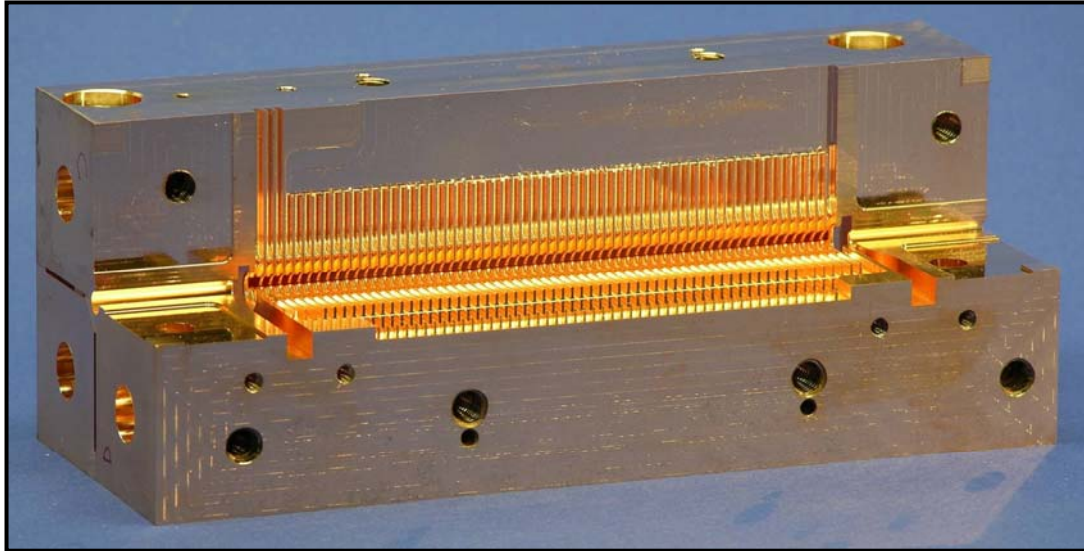

HDS60

$\langle E_{acc} \rangle$ [MV/m]	150
f [GHz]	29.985
$\Delta\phi$ [°], l_c [mm]	60, 1.66635
$a_{1,2}$ [mm]	1.9, 1.6
$d_{1,2}$ [mm]	0.55, 0.55
$Q_{1,2}$	2356, 2316
$r/Q_{1,2}$ [LinacΩ/m]	29000, 34000
$v_g/c_{1,2}$ [%]	8.0, 5.1
$\langle a \rangle / \lambda$	0.175
N	2.45×10^9
L_{bx} [m ²]	1.02×10^{34}
N_c, l [mm] (active)	60, 100
N_s	12
N_b	160
τ_p, τ_f [ns]	68.4, 5.2
P_{in}, P_{out} [MW]	98, 64.5
η [%]	13.9





Overview of recent 30 GHz results



Reached nominal 30 GHz CLIC values :

150 MV/m 70 ns

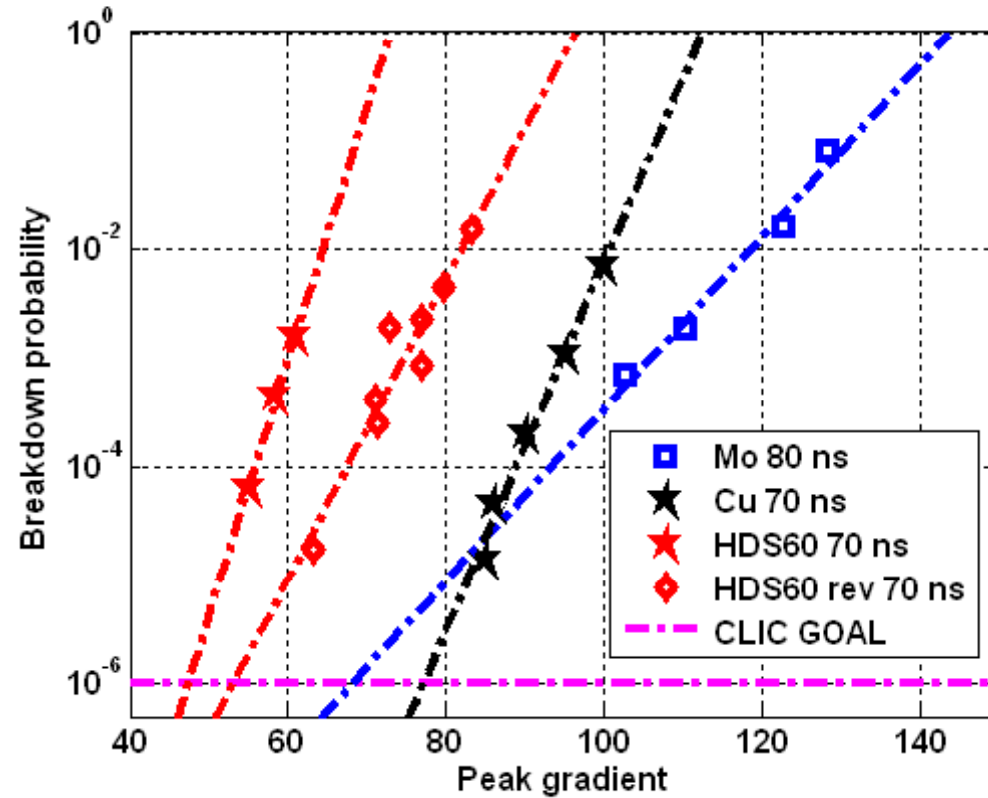
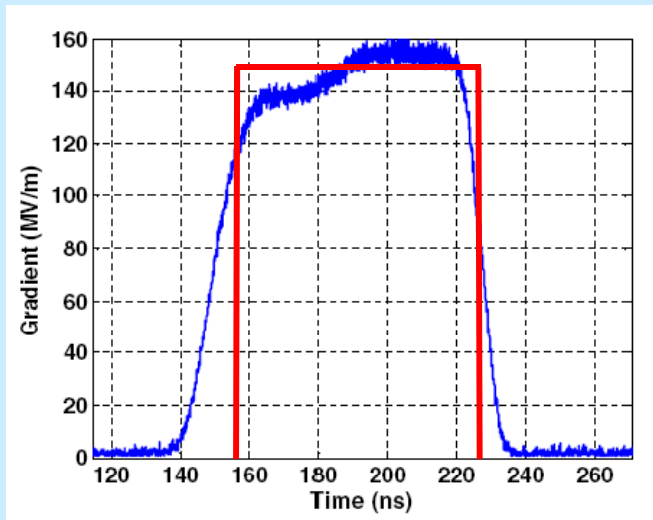


Molybdenum shows higher gradient but different slope

HDS performs worse than round brazed structure



New Materials for High-Gradient

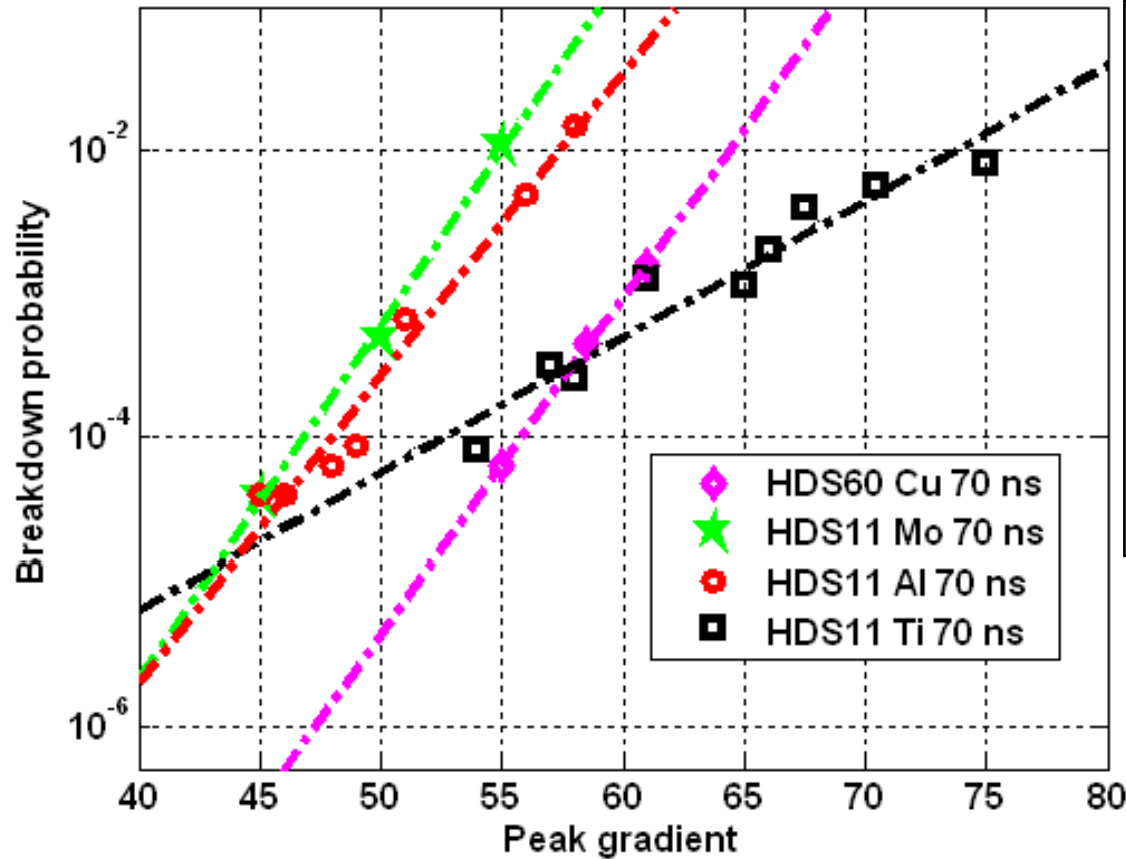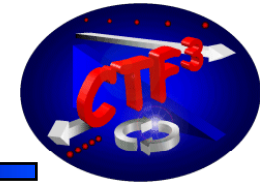

Copper has still the best performance at low break down rate











New Materials for High-Gradient




HDS11 Molybdenum

HDS11 Titanium

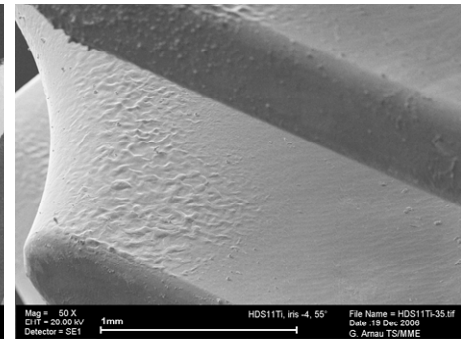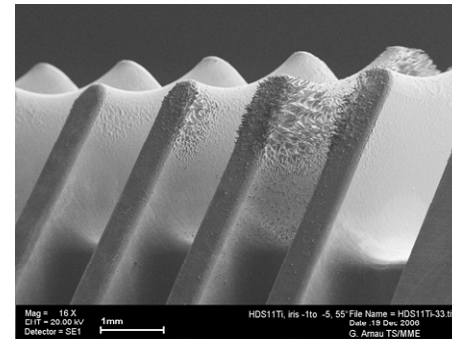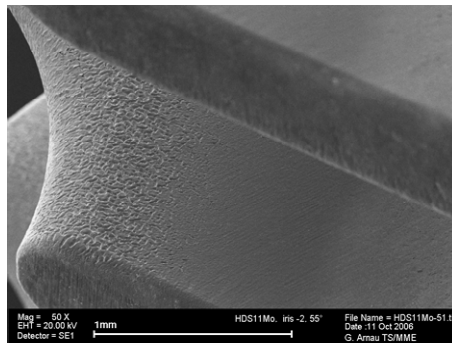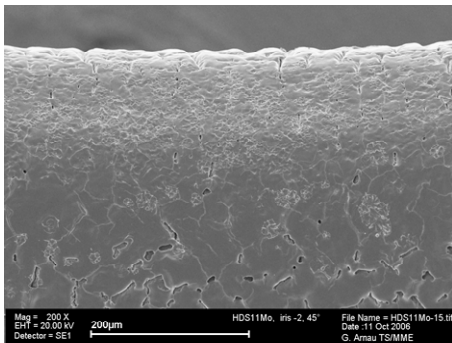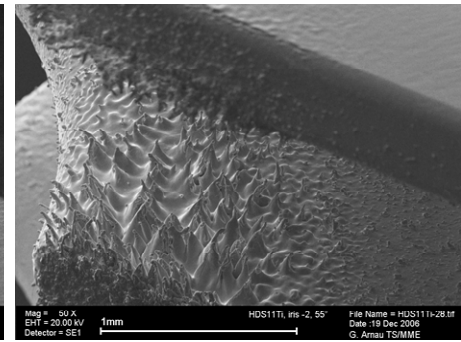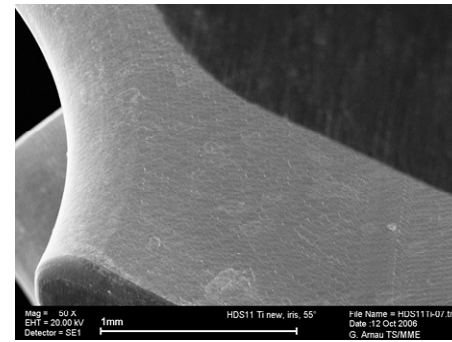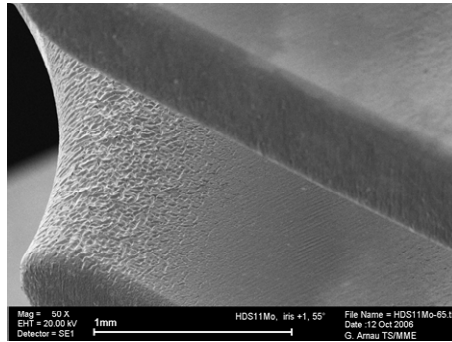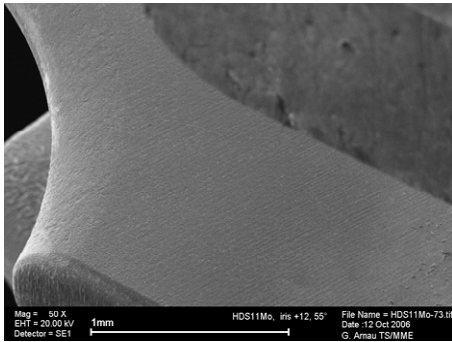




New Materials for High-Gradient

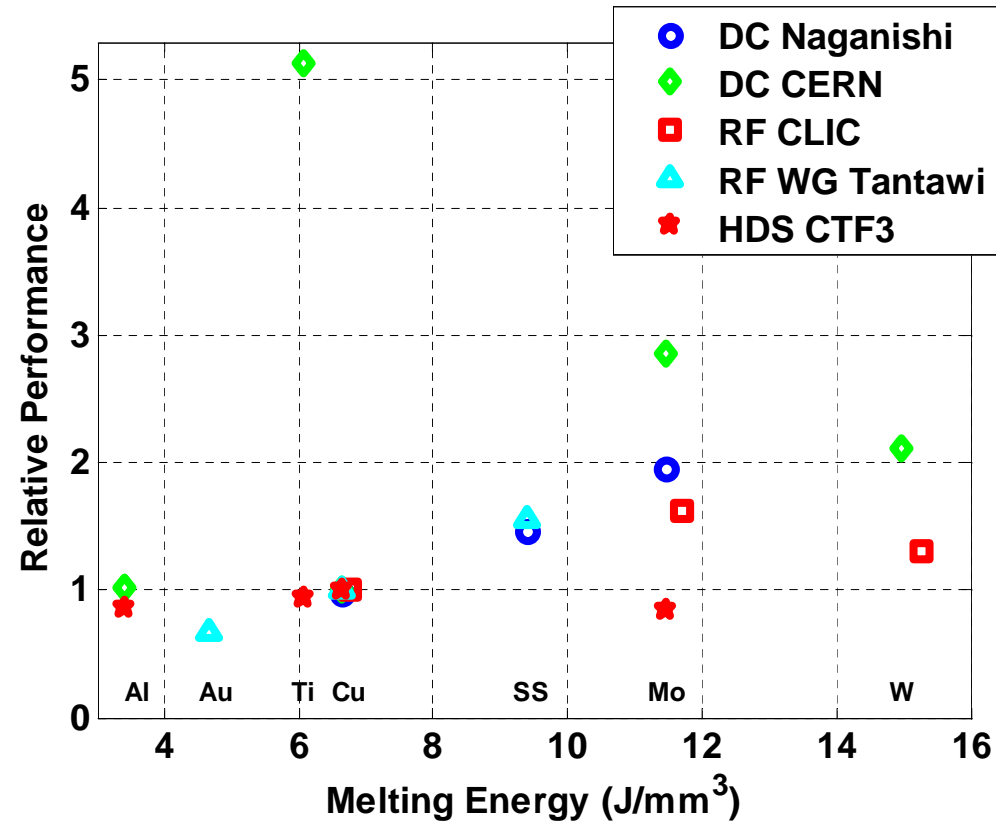



So far, most promising materials have higher melting energy/volume



11.4 GHz results and test facilities

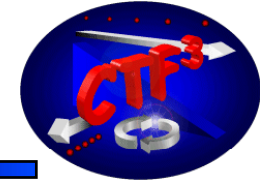


Test facilities based on
50 MW klystrons made
by SLAC or Toshiba
Developed for NLC/GLC

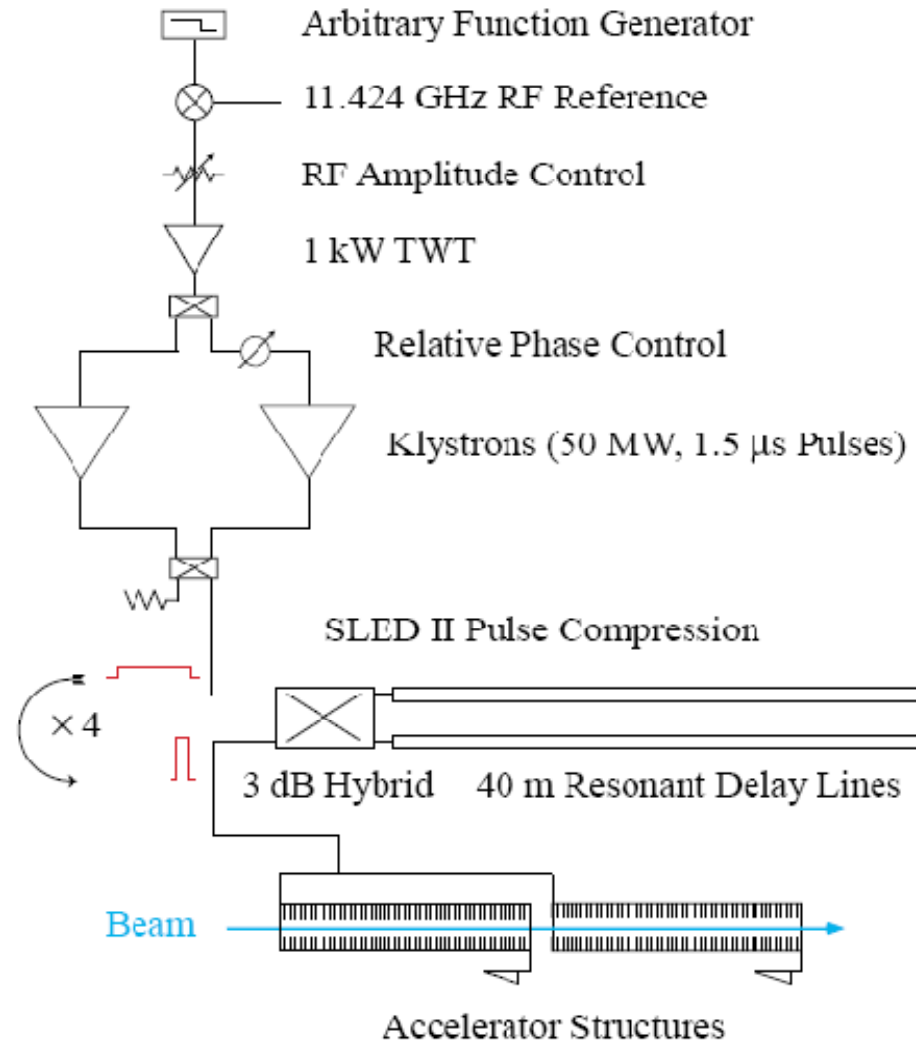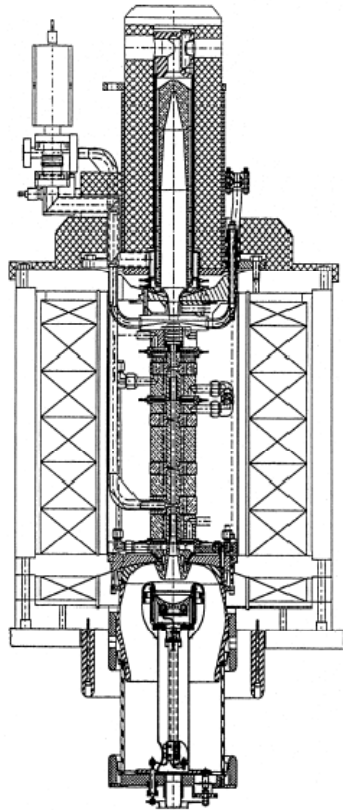




NLCTA X-band power source at SLAC


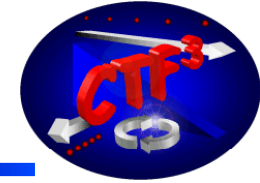


- 60 MeV electron beam for energy and phase measurement
- 3 Test Stations:
2x50 MW into SLEDII,
300 MW for 2-4 slots
- Numerous test stands in the Klystron Test Lab
2 single Klystron test stands
2x50 MW into SLED II

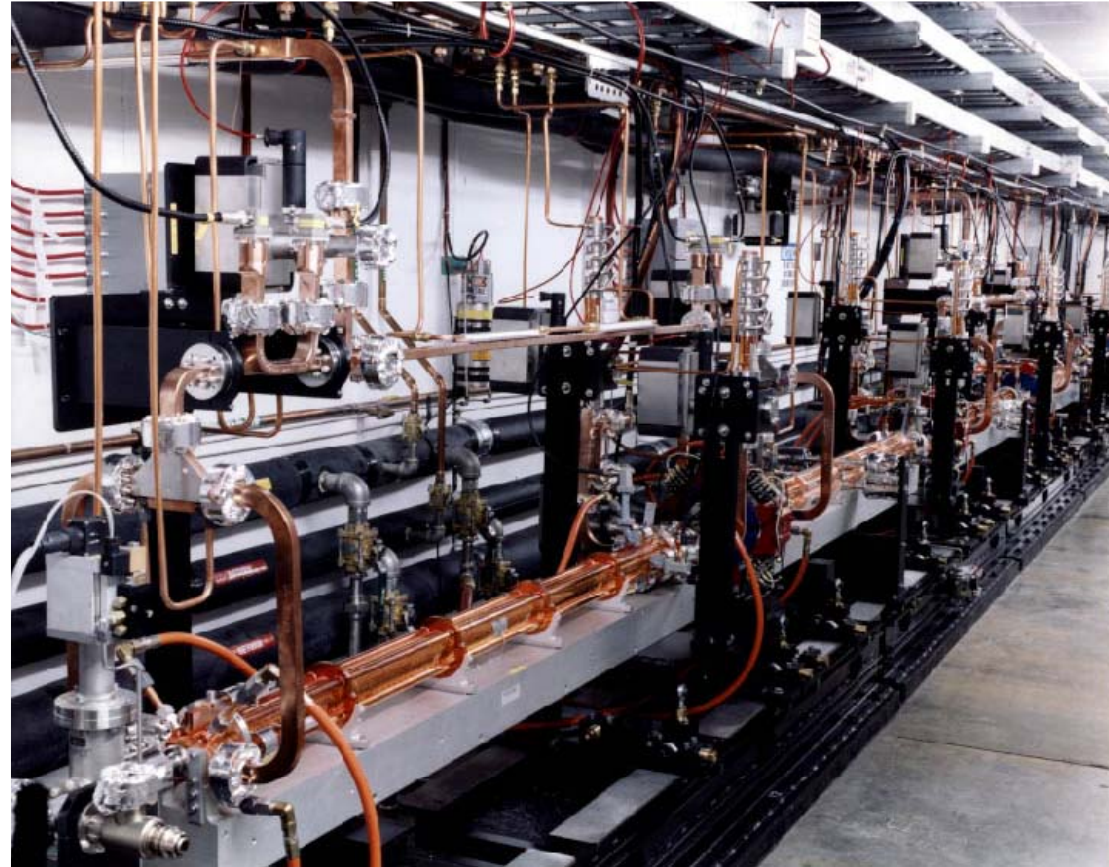



Typical Conditioning history

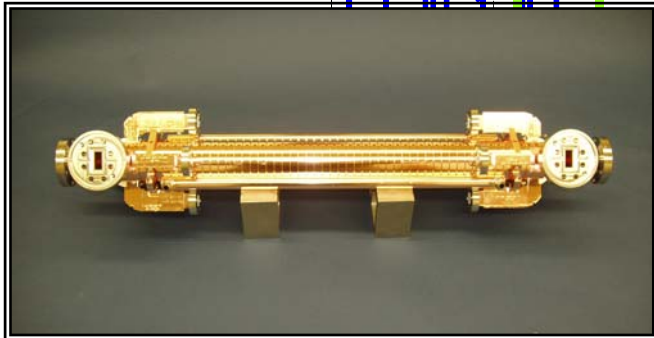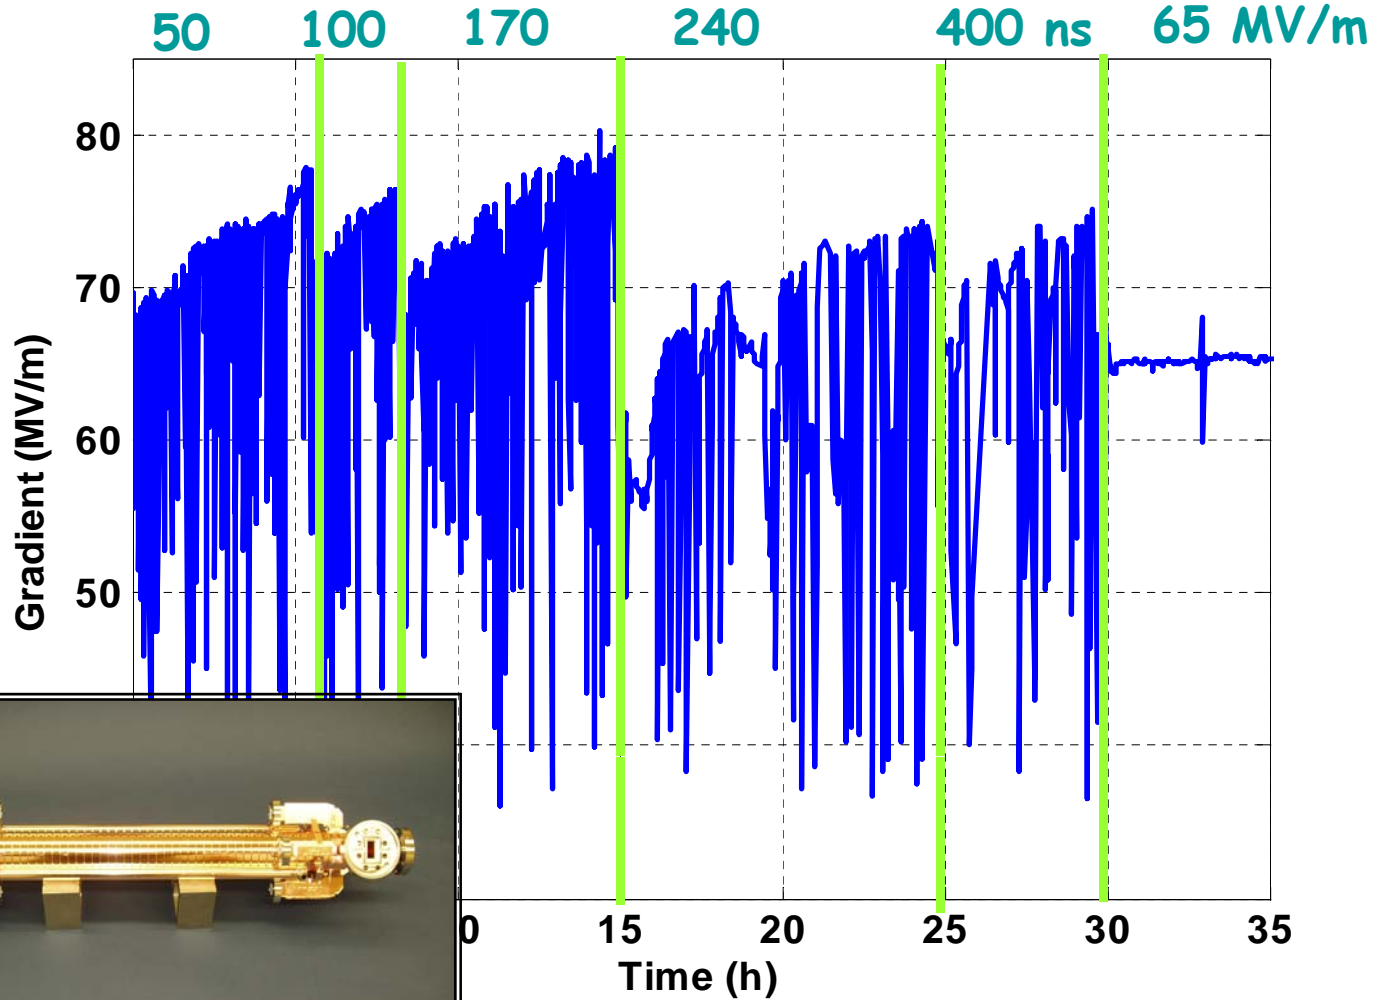





First CLIC x-band structure



One tested at KEK and one tested at SLAC

Beam hole radius	3 mm
Disk thickness	2 mm
Effective length (26+2cells)	.2449 m
Group velocity, v_g/c	1.1% *
Impedance, r/Q	16.0 [k Ω /m]
Shunt impedance, r	106.8 [M Ω /m]
Q	6680*
Attenuation parameter	1.61 [neper/m]**
Filling time, t_f	58 [ns]**
Surface/Accelerating field	1.9

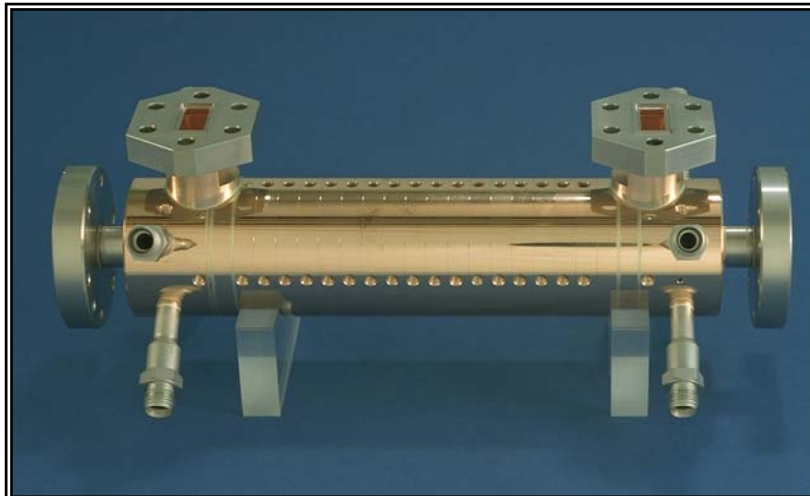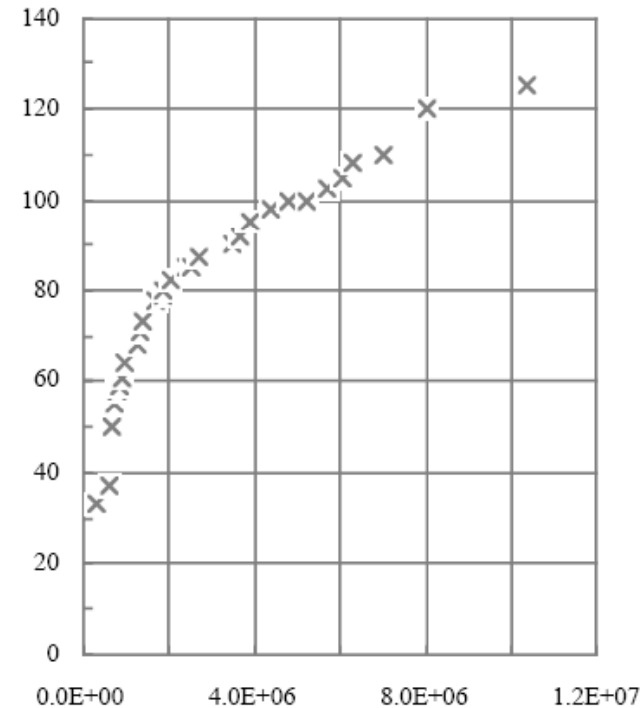





150 MV/m peak, 125 MV/m avg

150 ns pulse length

No breakdown monitoring




Round Clamped Iris Structures

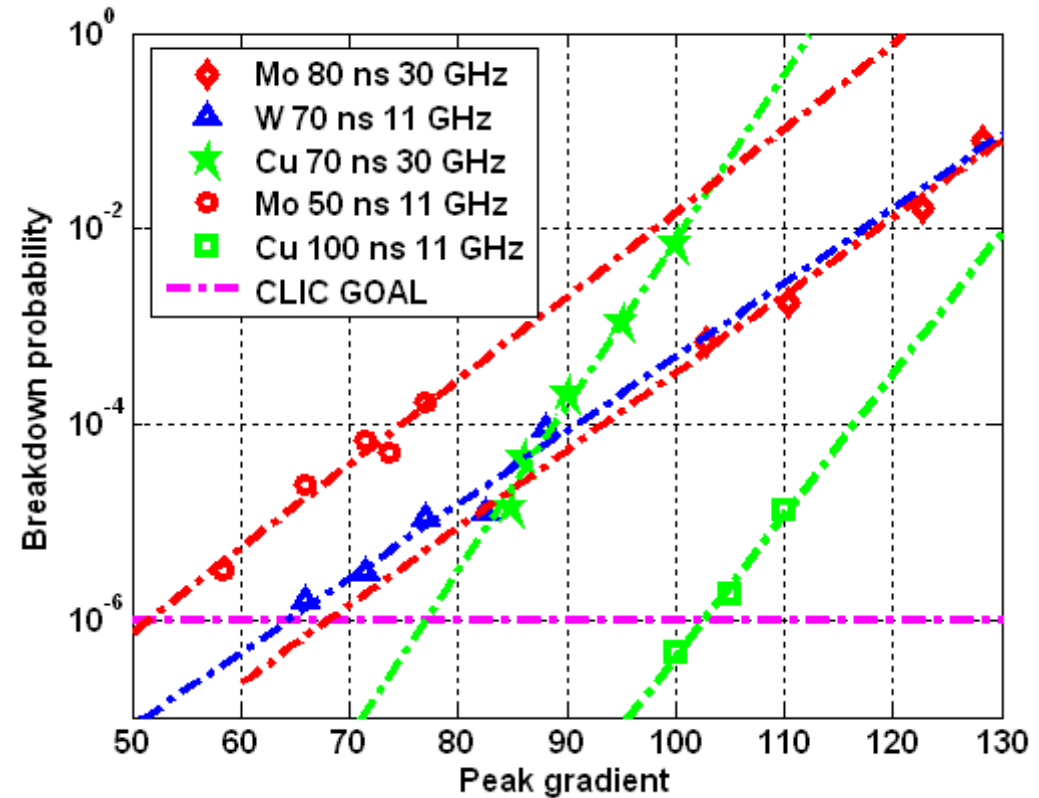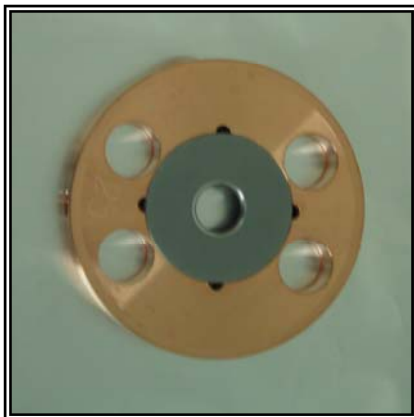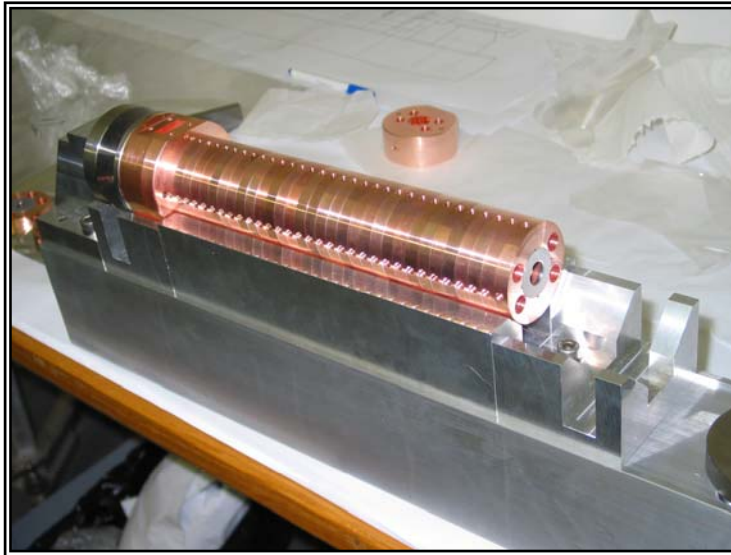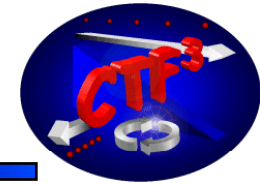


Superior gradient for new materials at x-band not confirmed
Shallower slope unique to clamped structures ?


HDX11, 11.424 GHz Structure for NLCTA

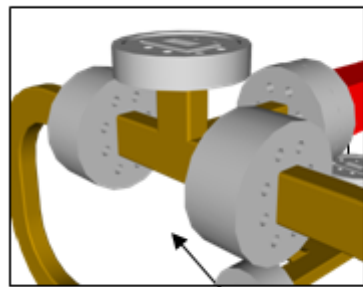




Input waveguide connection with SLAC Magic Tee

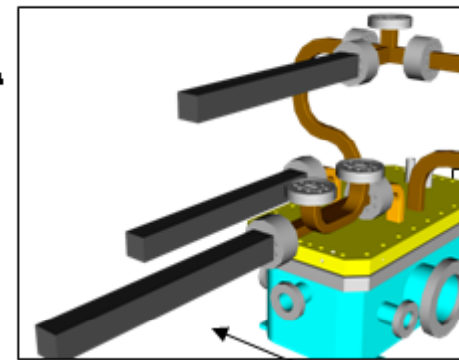


Waveguide terminations to Loads

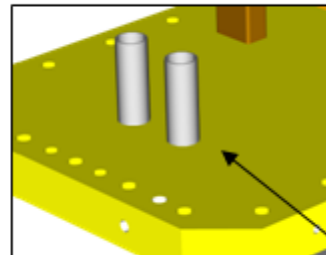


Water-cooling Connections (Ø16mm) Brazed to the cover plate

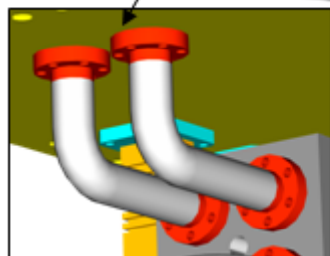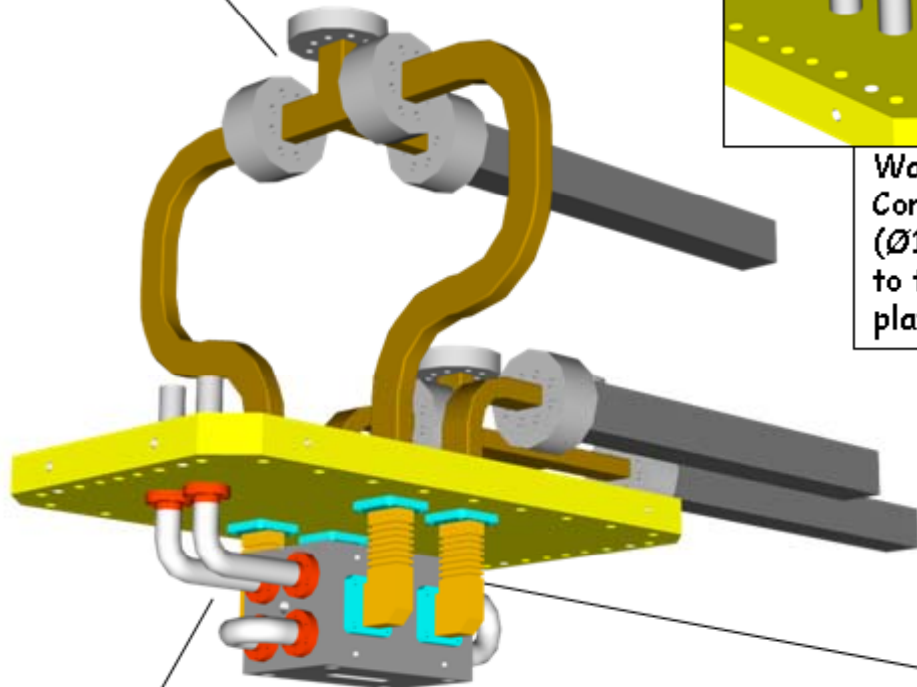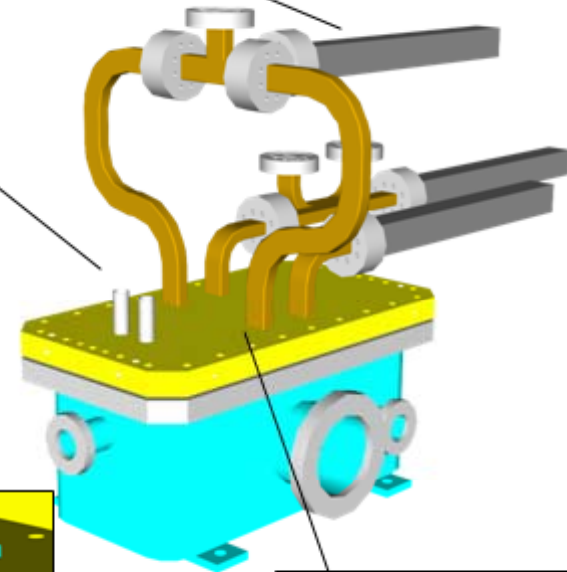


Water connections inside the vacuum can with Helicoflex Joints

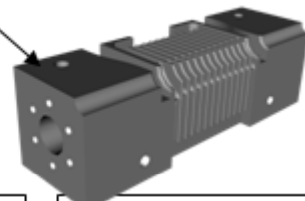

Structure based on HDS Technology

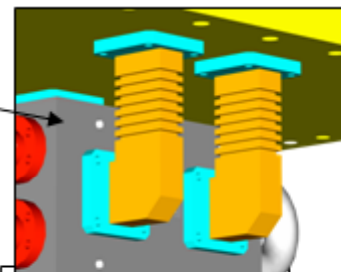



Waveguides in vacuum can with mitre bends

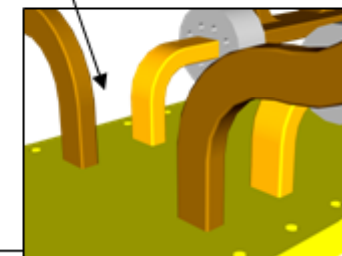

WR90 Waveguides Brazed to the cover plate




HDX11mo conditioning history so far

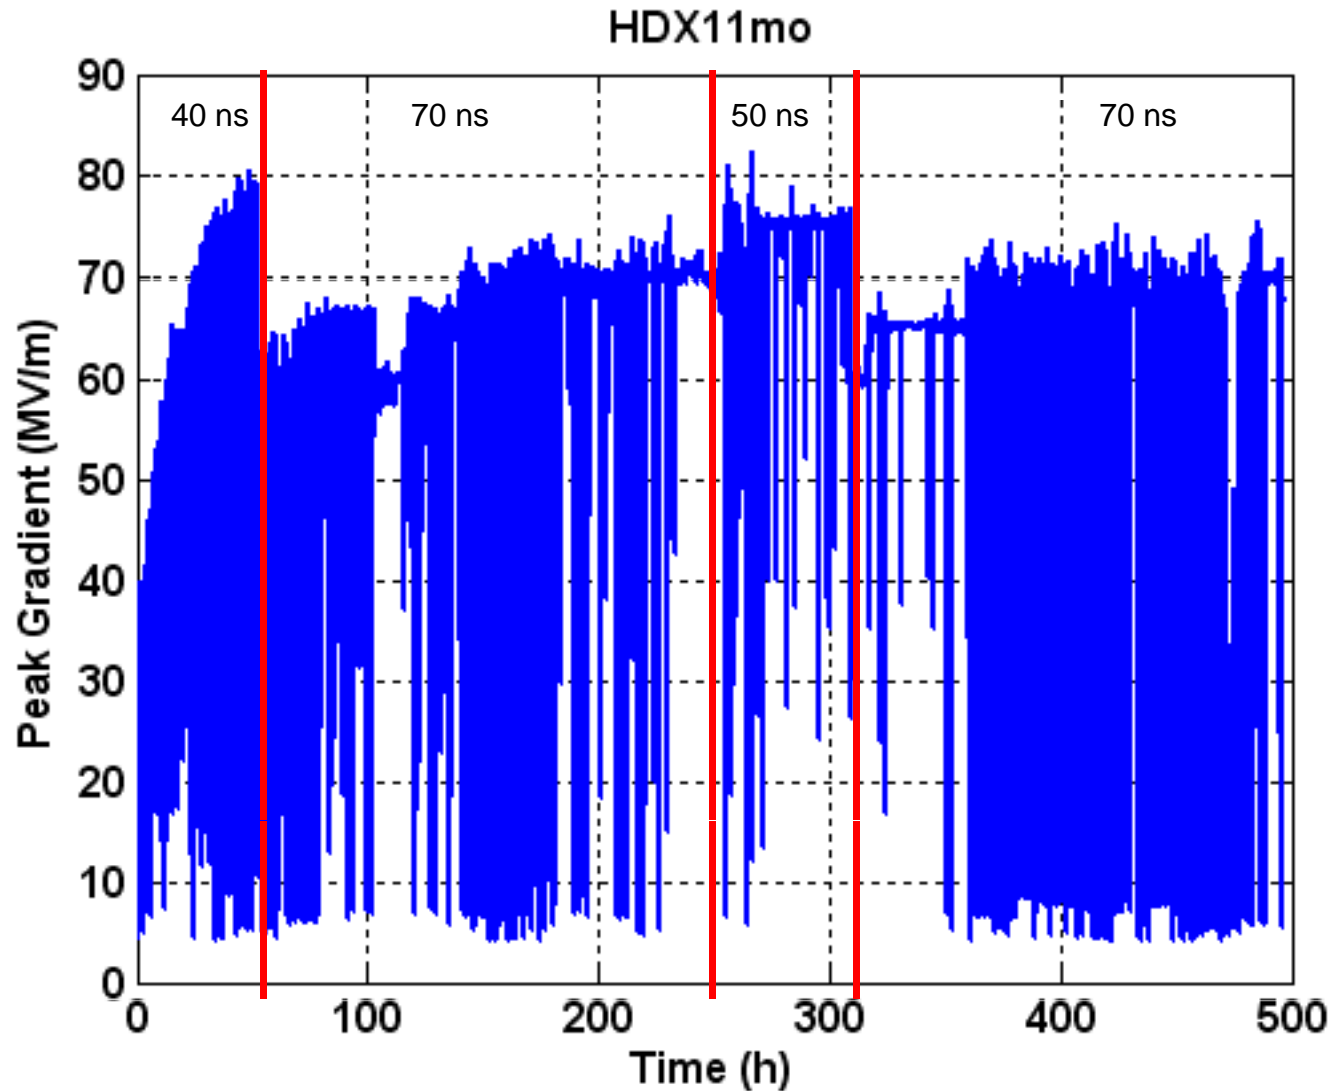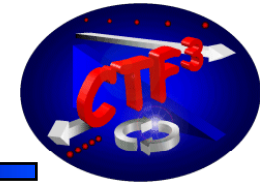





HDX11cu conditioning history

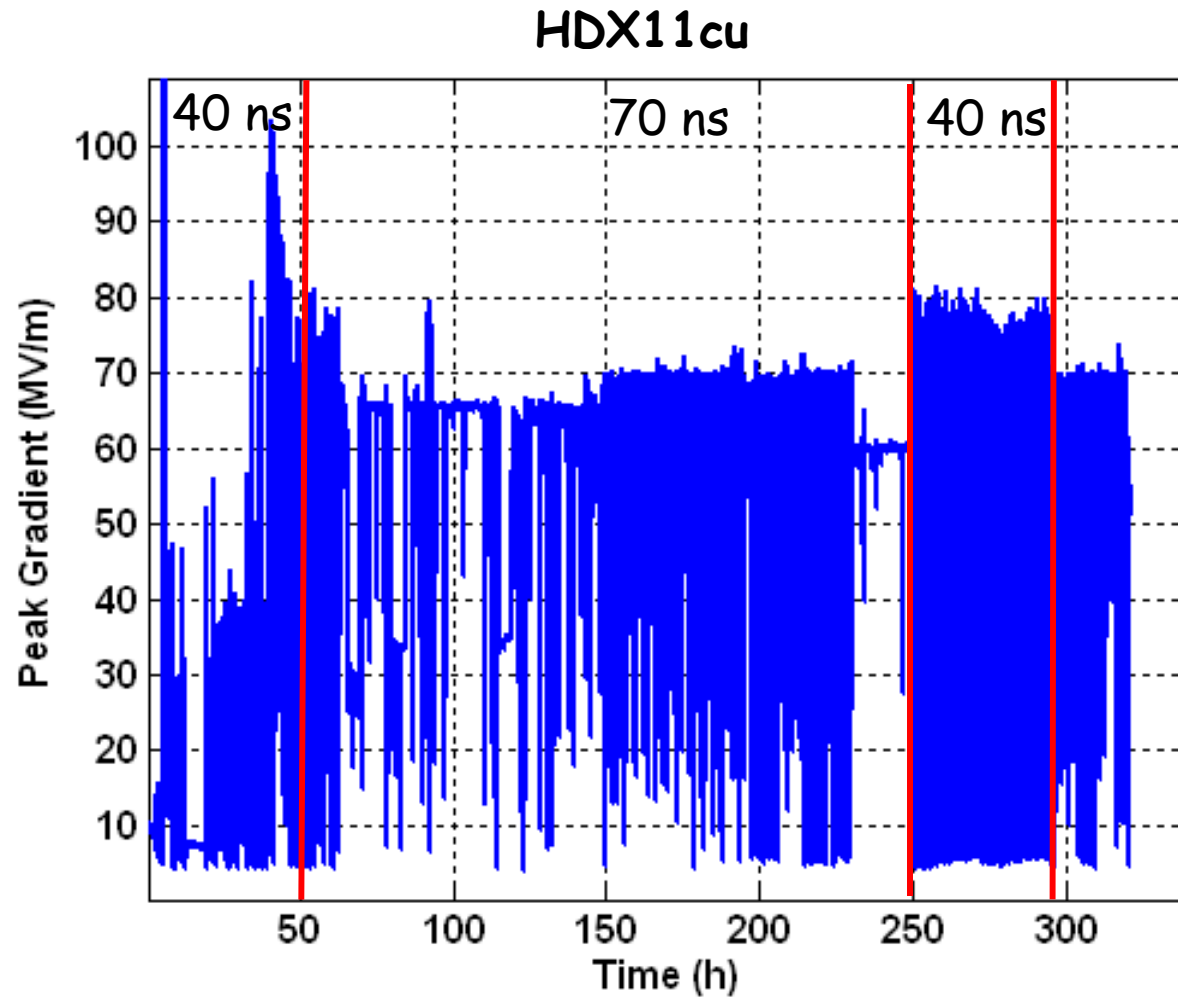



Hybrid damped structures (HDX) at x-band Frequency scaling

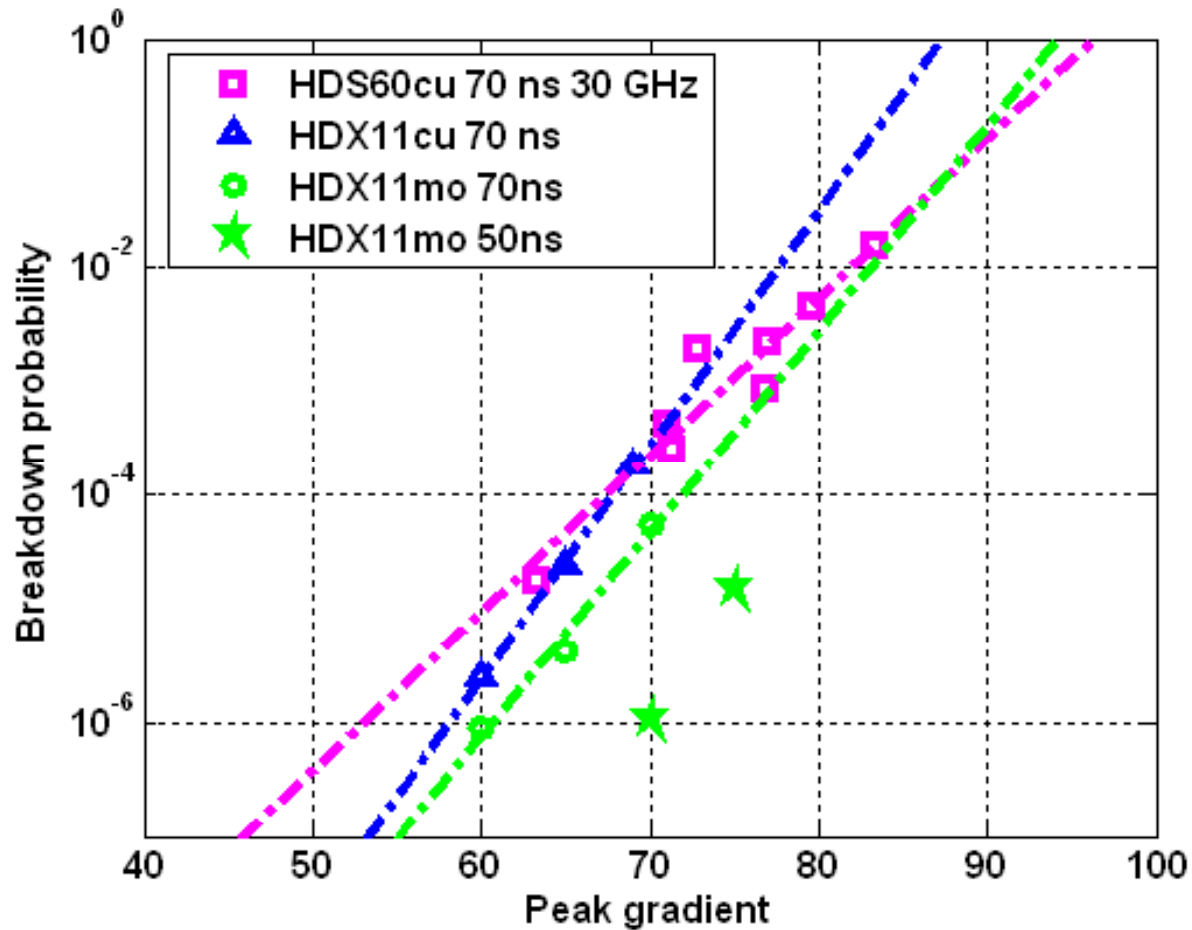
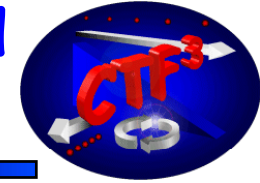


Scaled structures show very similar performance

HDS-type structures show consistently limited performance




Post mortem inspection of HDX11cu

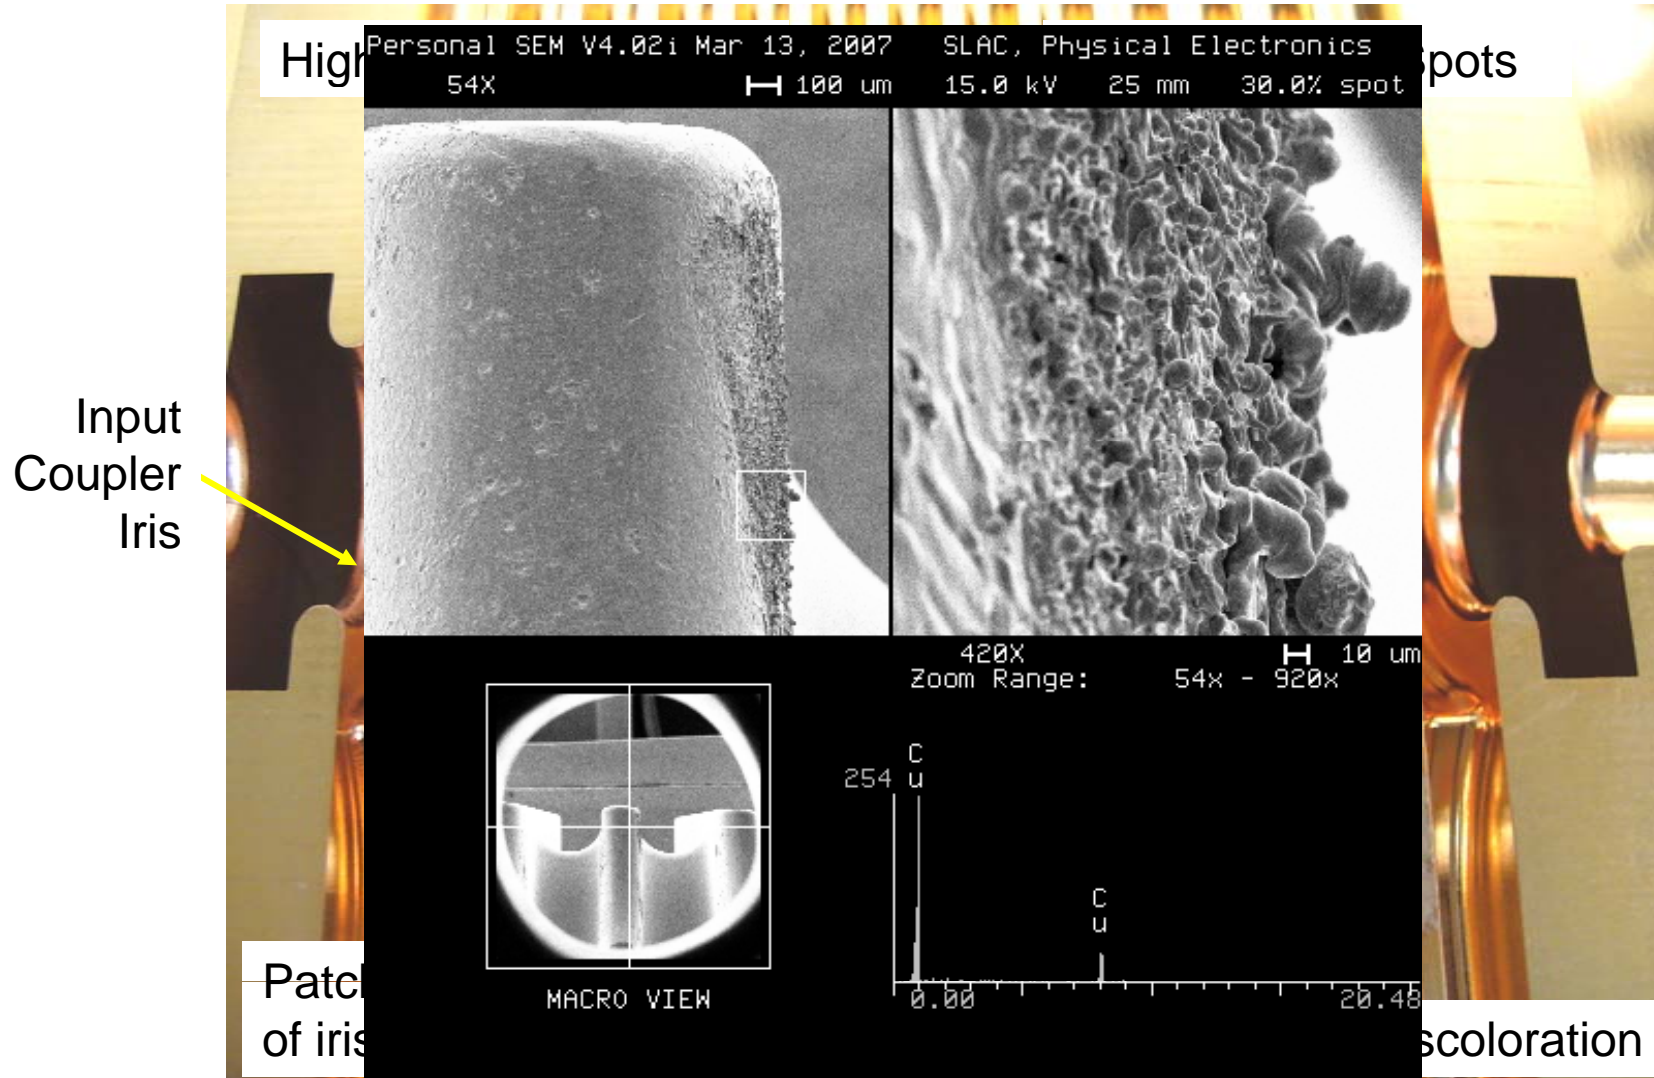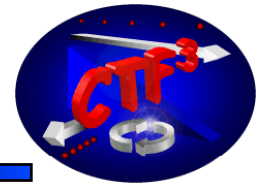




A reference structure for CLIC from NLC

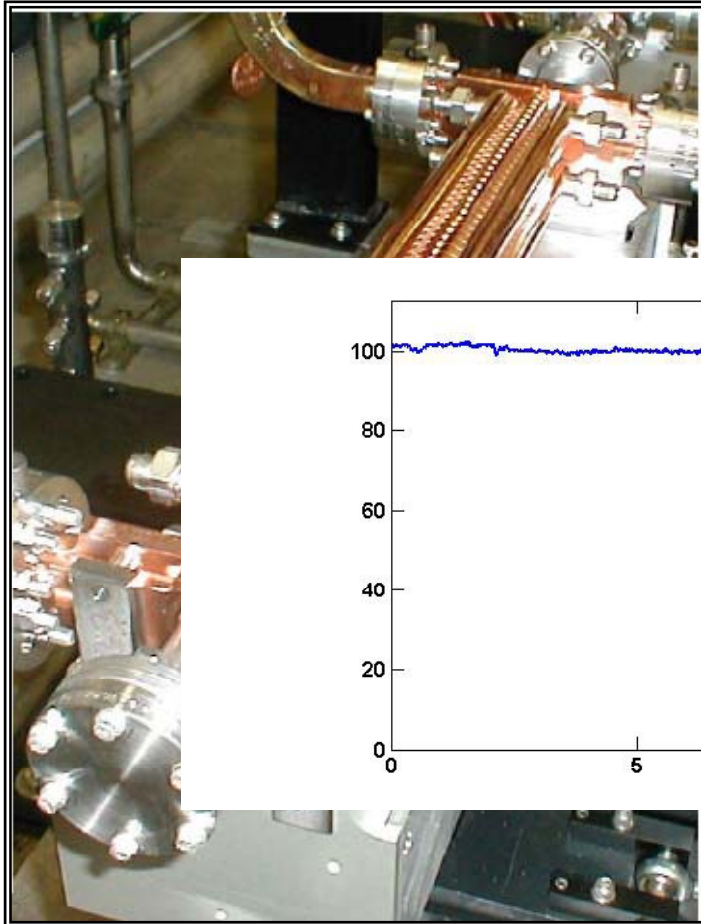

Length: 53 cm
Phase advance: 120 deg
Group velocity: 3 %
 a/λ : 0.13
 E_s/E_{acc} : 2.2
 P_{in} (65 MV/m): 41 MW
Coupler: mode launcher
Preparation: H-brazing,
diamond turning

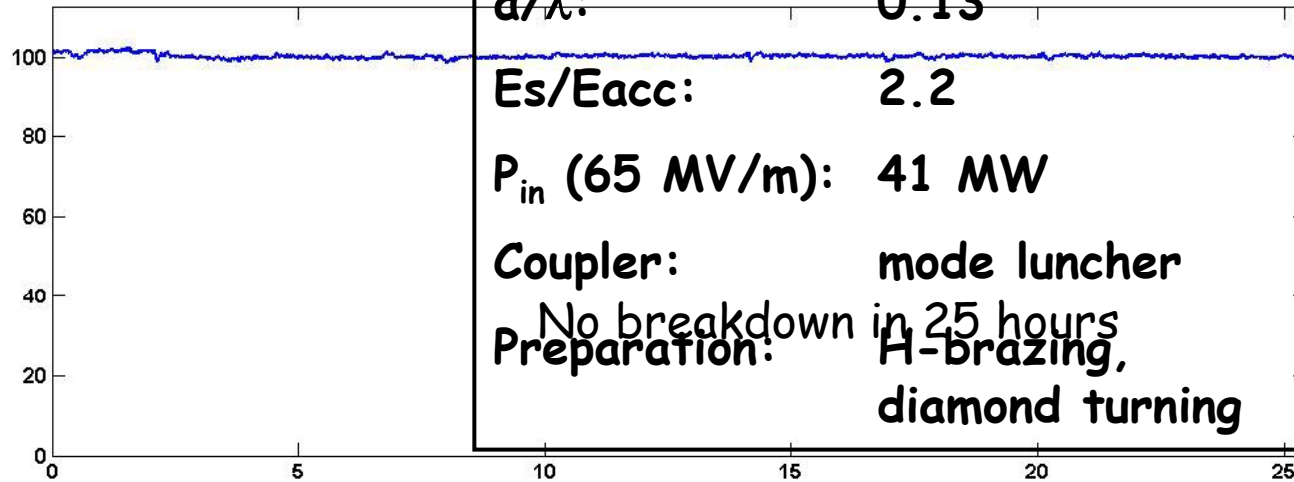




Tests of old NLC structures at short pulses




T53vg3MC can be used as a first reference for the new CLIC parameters

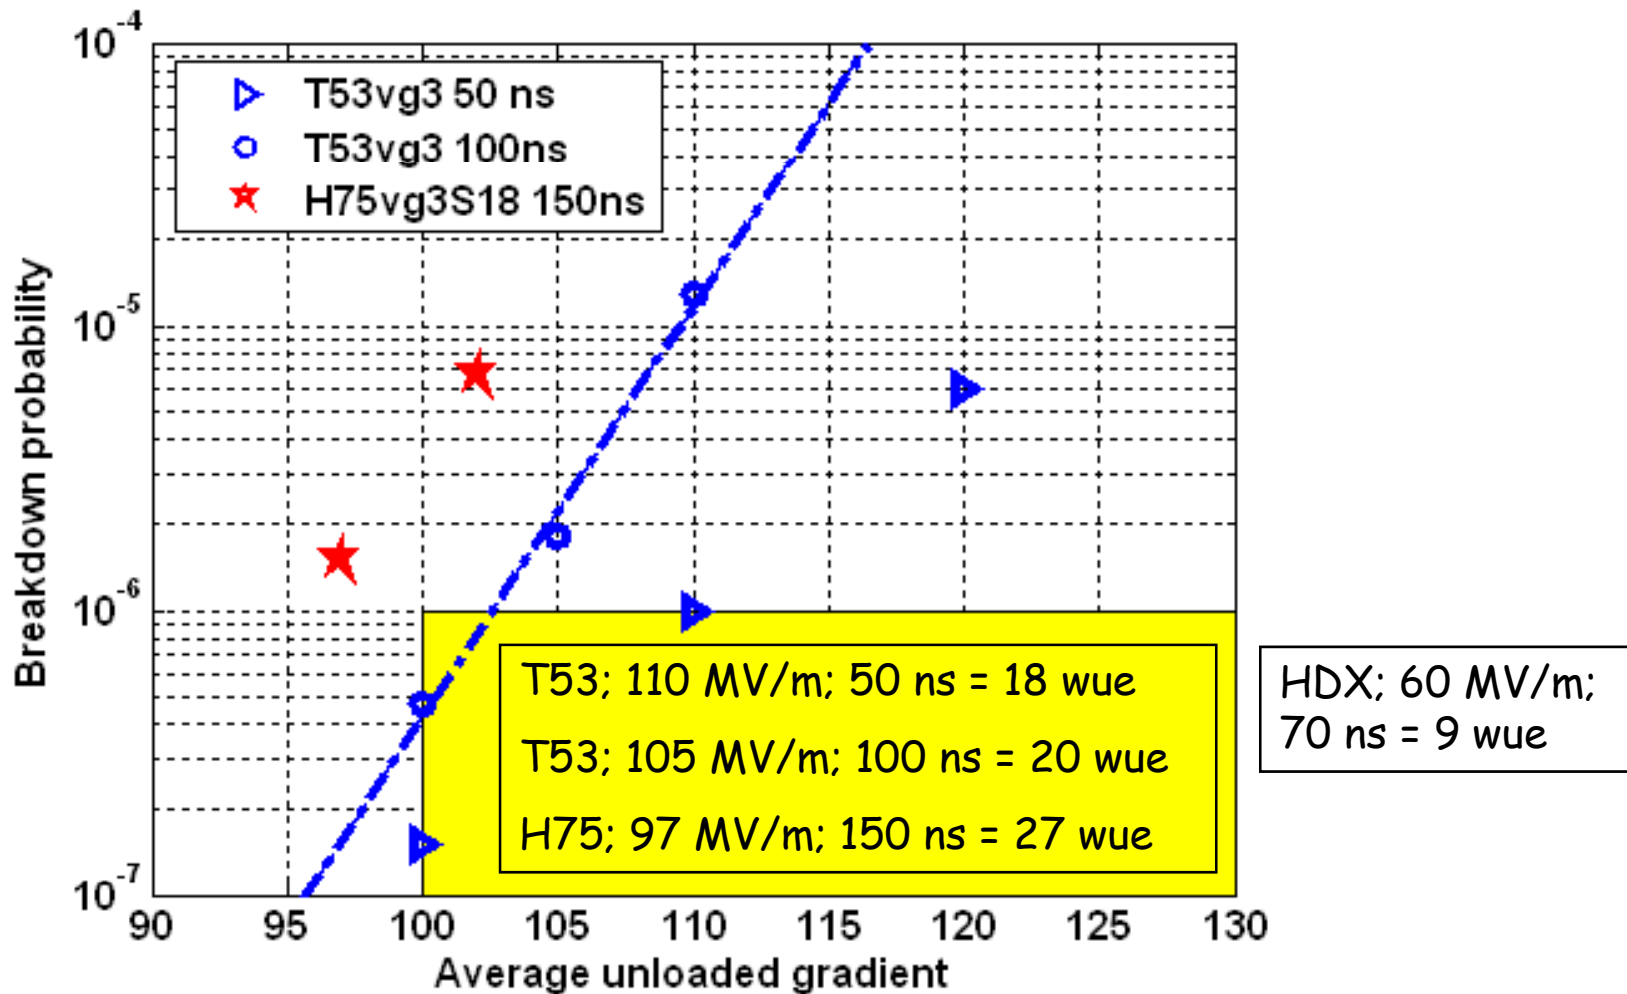



Pulse Length Dependence

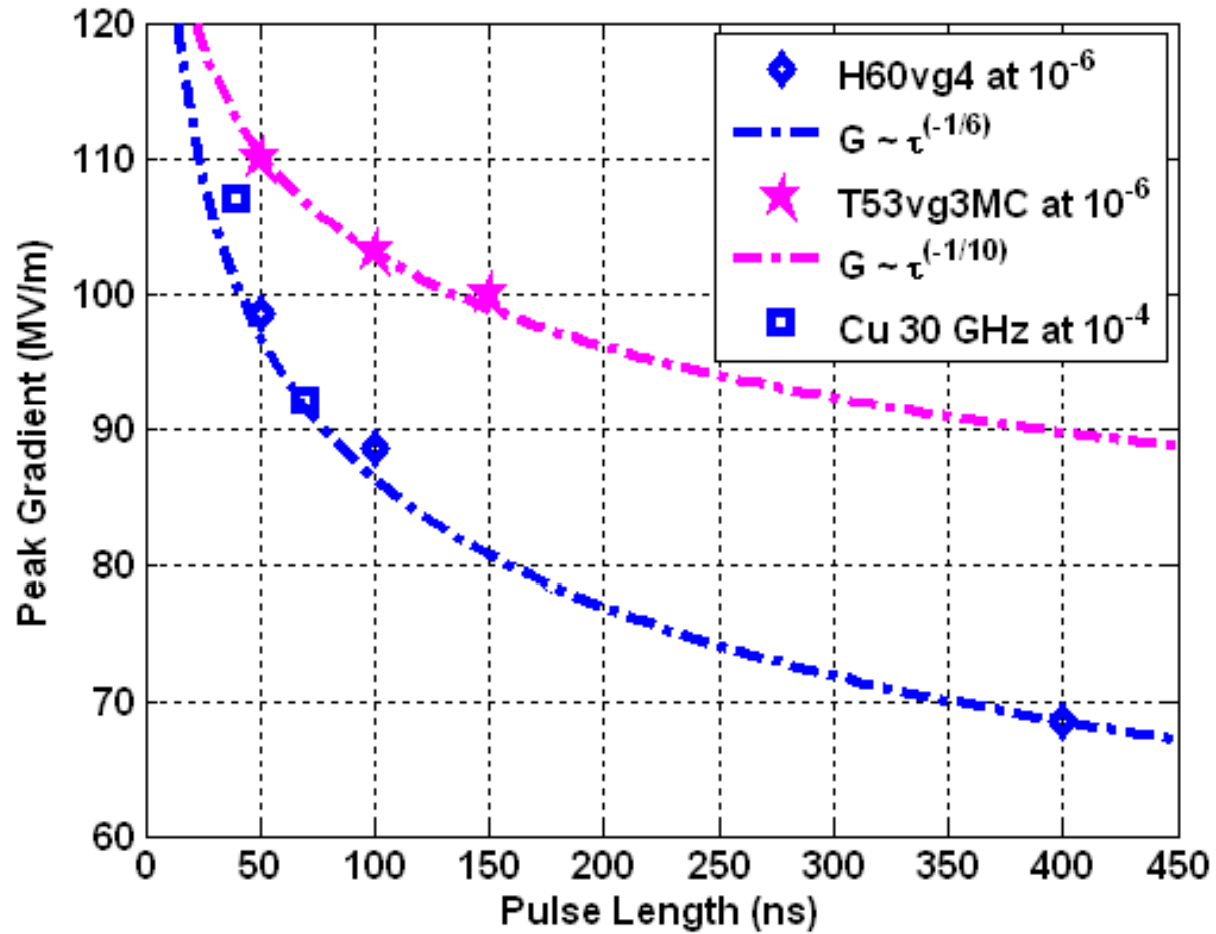



Conclusions on recent structure tests



- Current CLIC design within experimentally demonstrated region
- ✓ 27 wue have been measured (Design used 18)
- ✓ 130 MW input Power for 100 ns into first cell of T53
- The T53 could be used as a reference structure for CLIC
- Hybrid Damped Structures show performance deficit (short phase advance, slots, quadrants and milling)
- Copper is still the best material to make accelerating structures (Molybdenum still has some potential, shallow slope seen in previous experiments could be due to iris clamping, slow processing as usual)
- Exactly scaled structures seem to perform independent of frequency (therefore 30 GHz test are still meaningful)
- Structure manufacturing technology seems to play an important role Damping has to be integrated and tested



Healthy Collaborations



CLIC structure: SLAC KEK Saclay

We are the hot topic !


SLAC * today

Tuesday - May 8, 2007

SLAC And CERN Collaborate in Testing a New Accelerator

by Maria José Viñas

Parts of the Compact Linear Collider (CLIC)—CERN's experimental project to accelerate electrons in a unique and powerful way—are currently being tested at SLAC. Raquel Fandos, an electrical engineer from CERN, is using SLAC's Next Linear Collider Test Accelerator (NLCTA) in Endstation B to conduct trials of prototype accelerator structures that would be used at CLIC. This research is part of the CLIC feasibility study expected to be completed in 2010.



Raquel Fandos, an electrical engineer from CERN, in the Next Linear Collider Test Accelerator control room at SLAC where she conducts experiments.

Fandos' group at CERN wants to build radio-frequency accelerator structures that work at a gradient of 100 MV/m (accelerating electrons up to 100 MV per meter of machine) and produce 70-nanosecond pulses. "We have already reached those parameters with some structures," says Fandos. "However the breakdown probability is still too high, and we observe damage on the surface of the structures after a few weeks of testing." This is why Fandos is currently testing the sturdiness of different accelerator structures at the NLCTA, applying different combinations of pulse lengths and gradients in each trial to observe how many breakdowns occur in the devices in a certain period.

This is the third time in two-and-a-half years that CERN personnel have come to SLAC to test CLIC parts, and Fandos says the collaboration between the two centers will probably increase in the future. Although CLIC was initially designed to work at an accelerating frequency of 30 GHz (the same level at which the test facility at CERN works), CERN recently decided to switch CLIC's frequency to 12 GHz, very close to the 11.424 GHz at which NLCTA operates, making the facilities at SLAC uniquely suited for testing the components of CLIC.

ILC-News Letter

In the News

From *SLAC Today*
8 May 2007
SLAC and CERN Collaborate in Testing a New Accelerator
Parts of the Compact Linear Collider (CLIC)-CERN's experimental project to accelerate electrons in a unique and powerful way—are currently being tested at SLAC.
[Read more...](#)





12 GHz stand alone power source



12 GHz power source: PSI INFN-Frascati Trieste

Based on a scaled 11.4 GHz klystron

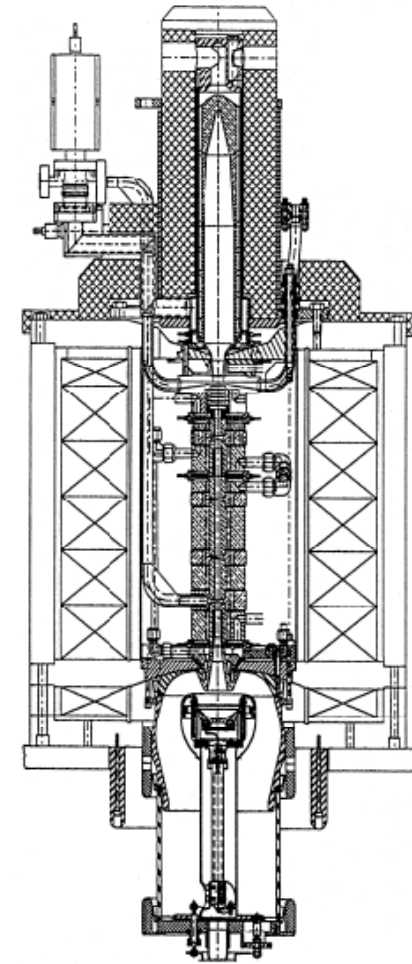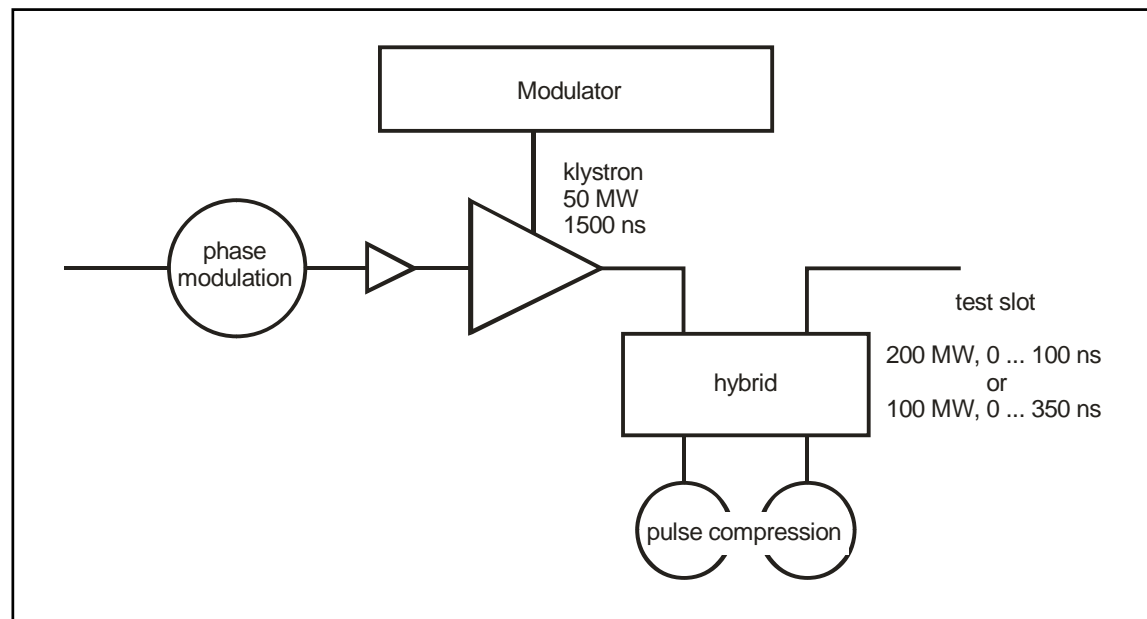

Independent 24/7 testing with fast turn around


Variable pulse length

Long term testing

Synchronized with CTF3



Future Testing Program




- 2007: Study Parameter Space at 30 GHz and testing of real structures at 11 GHz (focus on copper structures)
- 2008: Focus on two main geometries, develop damping, optimize structure
- 2009: CLIC prototype structure
- 2010: Longer term testing and better statistics

Number of tests (optimistic)

	2007	2008	2009	2010	sum
30 GHz	5	3	0	0	8
12 GHz	0	1	4	4	9
11.4 GHz	2	4	4	4	14
Stand alone at CERN	0	0	8	8	16
sum	7	8	16	16	47



30 GHz program in CTF3

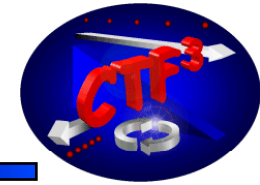

30 GHz will be used for fundamental studies of rf designs, preparation methods and materials

30 GHz:

- $\pi/2$ structure (test of short phase advance, fabrication tech.)
- HDS 11 copper/molybdenum (for better statistics)
- HDS 11 very small ($r=1.2$) (clear P/C experiment without other changes)
- Round 3.5 mm made out of quadrants (clear experiment for fab. Tech.)
- HDS4_150deg_thick_r=1.75 (iris thickness, phase advance, length, P/C)
- HDS4_150deg_thick_clean (compares cleaning with previous)
- NDS4_150deg_thick_r=1.75 (fab. Tech between HDS and NDS quadrants)
- NDS4_150deg_thin (iris thickness in comparison with NDS4_150deg_thick)
- Coupler test structure (not defined yet)




The two relevant geometries for the CLIC R&D program




	CLIC	CLIC_vg1	T26vg3 damped
Frequency: f [GHz]	12	12	11.424
Average iris radius/wavelength: $\langle a \rangle / \lambda$	0.12	0.128	0.134
Input/Output iris radii: $a_{1,2}$ [mm]	3.87, 2.13	3.87, 2.53	3.89, 3.17
Input/Output iris thickness: $d_{1,2}$ [mm]	2.66, 0.83	2.66, 1.25	1.66
Group velocity: $v_g^{(1,2)}/c$ [%]	2.39, 0.65	2.4, 0.95	2.86, 1.42
N. of cells, structure length: N_c, l [mm]	24, 229	18, 179	30, 265
Bunch separation: N_s [rf cycles]	8	8	8
Number of bunches in a train: N_b	311	359	66
Pulse length, rise time: τ_p	297	295	102
Input power: P_{in} [MW]	65	70	111
Max. surface field: E_{surf}^{max} [MV/m]	298	283	216
Max. temperature rise: ΔT^{max} [K]	56	58	25
Efficiency: η [%]	23.8	20	10.3
Bunch population: N	4.0×10^9	4.0×10^9	4.0×10^9



Parameters along the structures

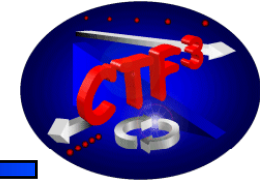


CLIC_vg3/1 is more extreme in maximum surface field, pulsed heating and lowest group velocity

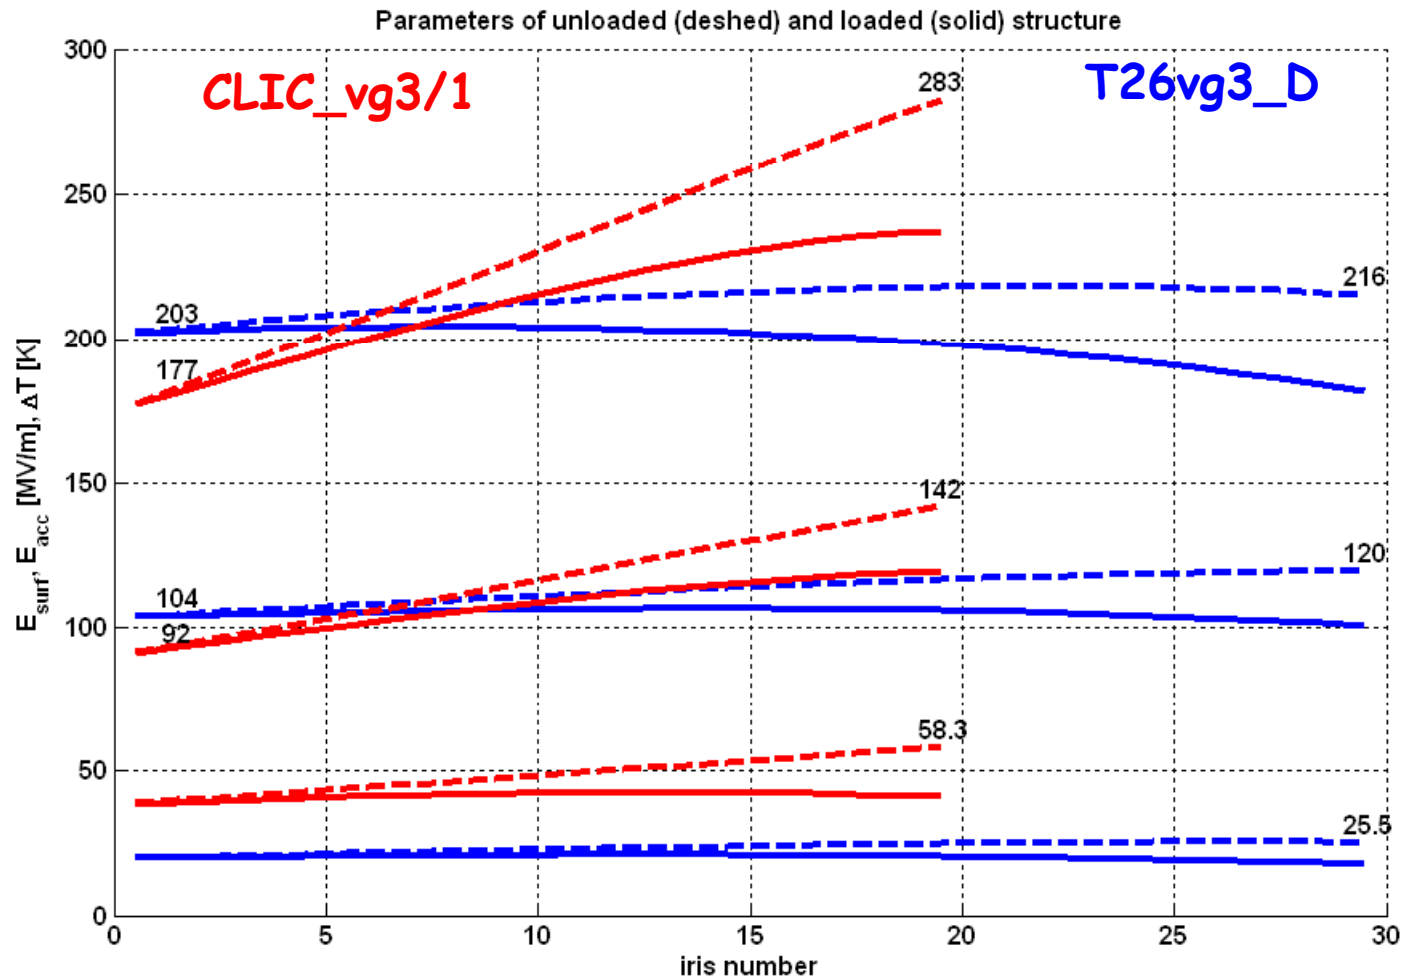



Efficiency milestones

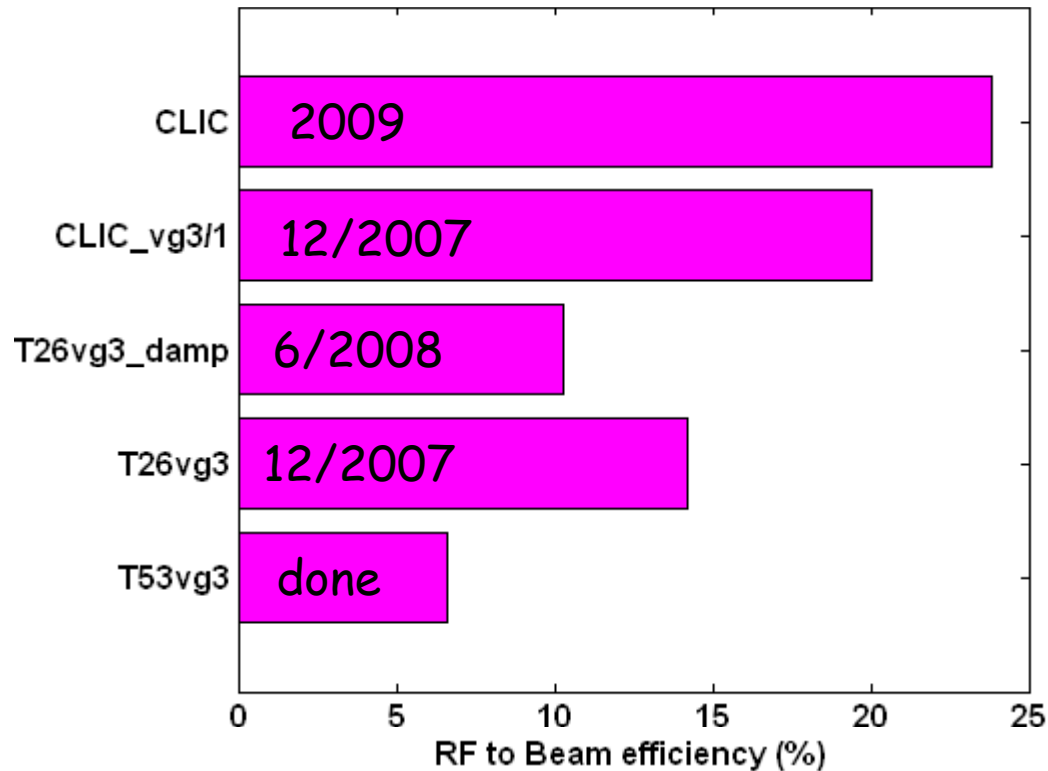

$P = 65 \text{ MW}; 297 \text{ ns} \Leftrightarrow \text{nb} = 311$

$P = 70 \text{ MW}; 295 \text{ ns} \Leftrightarrow \text{nb} = 359$

$P = 111 \text{ MW}; 102 \text{ ns} \Leftrightarrow \text{nb} = 66$


$P = 102 \text{ MW}; 113 \text{ ns} \Leftrightarrow \text{nb} = 93$

$P = 134 \text{ MW}; 104 \text{ ns} \Leftrightarrow \text{nb} = 27$

100 MV/m loaded, 10^{-6} break down rate, $q_b = 4 \cdot 10^9$,
8 rf period bunch spacing, $P \cdot \text{pl}/C = 18 \text{ Wue}$




Tentative CERN x-band R&D program



When	Structure	Technology	Lab
Dec 2007	CLIC_vg1	quadrants, damped	CERN
	T26vg3MC	disks, brazed, undamped	SLAC/KEK
March 2008	CLIC_vg1	quadrants, undamped	CERN
	T26vg3MC	quadrants, undamped	CERN/SLAC/KEK
June 2008	CLIC_vg1	disks, brazed, undamped	CERN
	T26vg3MC	disks, brazed, damped	CERN/SLAC/KEK
2009	CLIC prototype	fully featured, best technology	CERN/SLAC/KEK



Conclusions

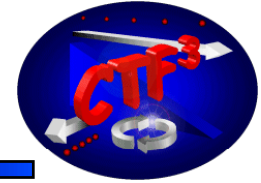



- ④ Good chance to demonstrate in time the new structure parameters
- ④ We are happy about our fruitful collaborations
- ④ Nevertheless busy and tight program to follow up
- ④ 12 GHz stand alone power source is essential for our program
- ④ We welcome your help



Even More Breakdown Rates




All HDS-type structures tested so far

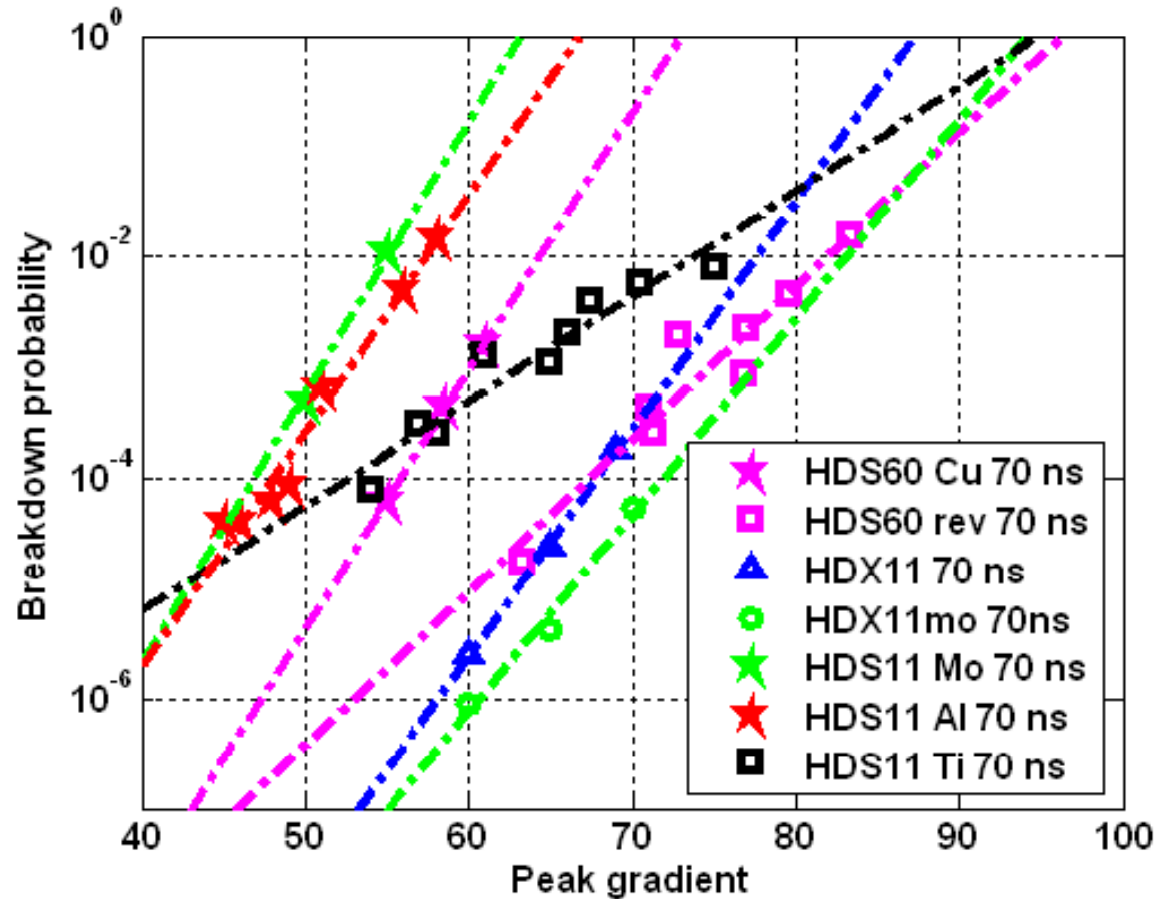

HDS performs consistently worse than round structures
No significant improvement for other materials over Copper





Parameters along the structures

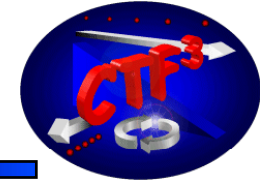

CLIC_vg3/1 is more extreme in maximum surface field, pulsed heating and lowest group velocity



CLIC_vg3/1

T26vg3_D

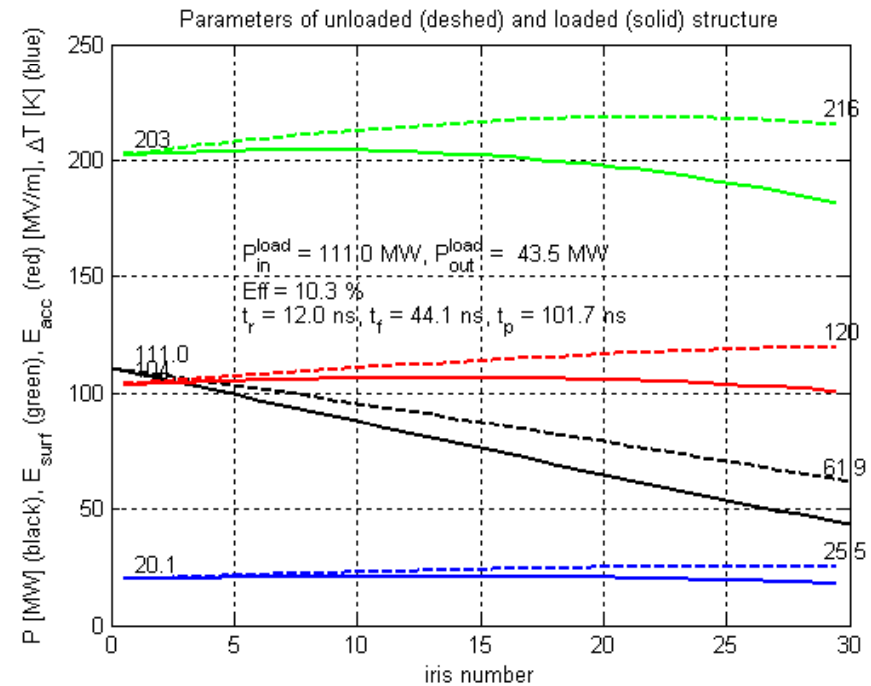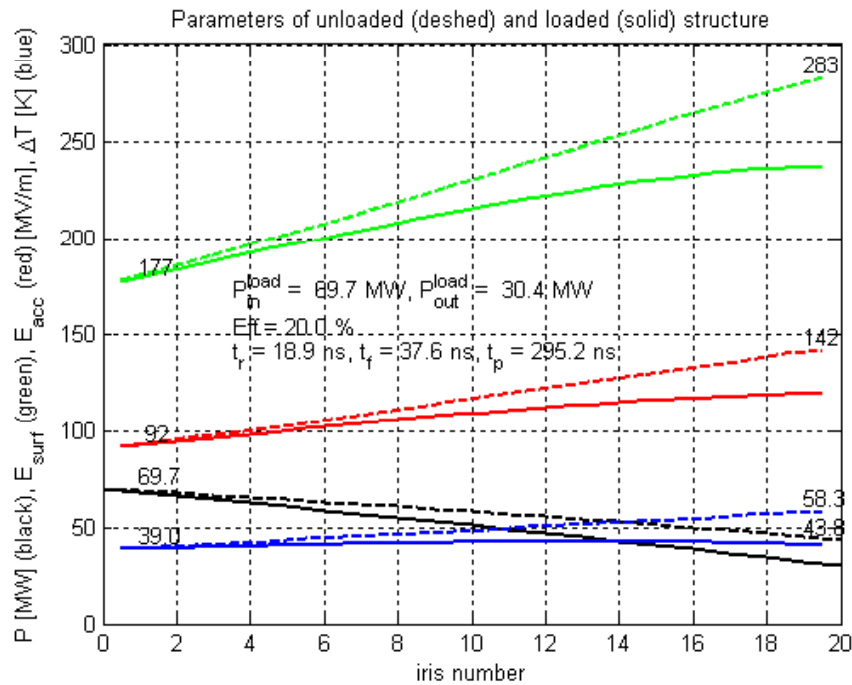



HDX11mo 75 MV/m, 50ns

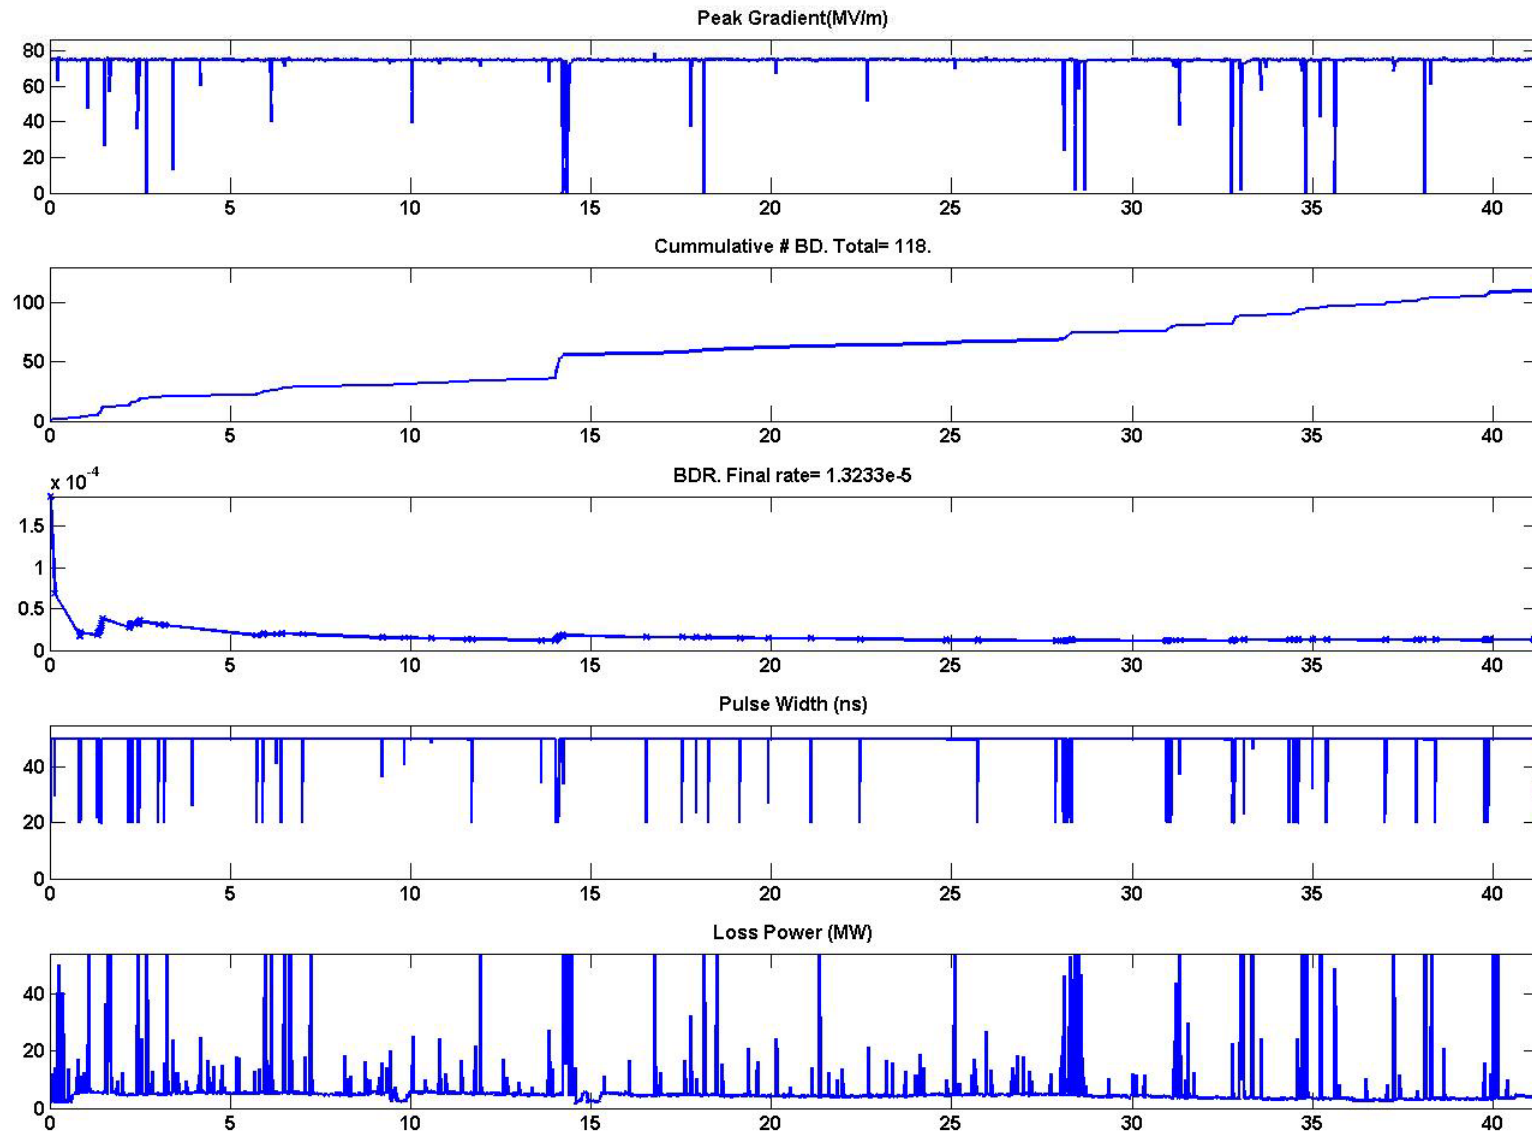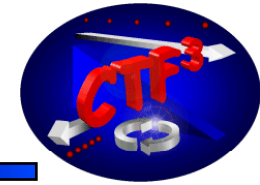




Comparing initial conditioning



Conditioning:

HDX11_Cu:	15 h,	40 ns,	80 MV/m
HDX11_Mo:	50 h,	40 ns,	75-80 MV/m
T53vg3MC:	10h,	50 ns,	120 MV/m (was previously conditioned to 95 MV/m
	2h,	50 ns,	80 MV/m
C30vg4_W:	40h,	30 ns,	80 MV/m
	90h,	30 ns,	110 MV/m
C30vg4_Mo:	>200h,	30 ns,	80 MV/m




Refractory metals condition slower than copper

Possible beneficial heat treatment is lost after weeks on air



HDX11 conditioning statistics

Or what it takes to break a structure

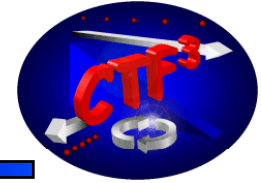

Copper:

- ~ 20000 Break downs
- ~ 50 hours initial conditioning
- ~ 600 hours
- Damaged


Molybdenum (preliminary):

- ~ 11500 Break downs
- ~ 500 h so far
- "most likely damaged too"



Duration: 6 weeks with 5 weeks experiment



Breakdown Rates

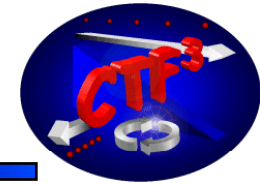

Frequency scaling experiment of 3.5 mm round

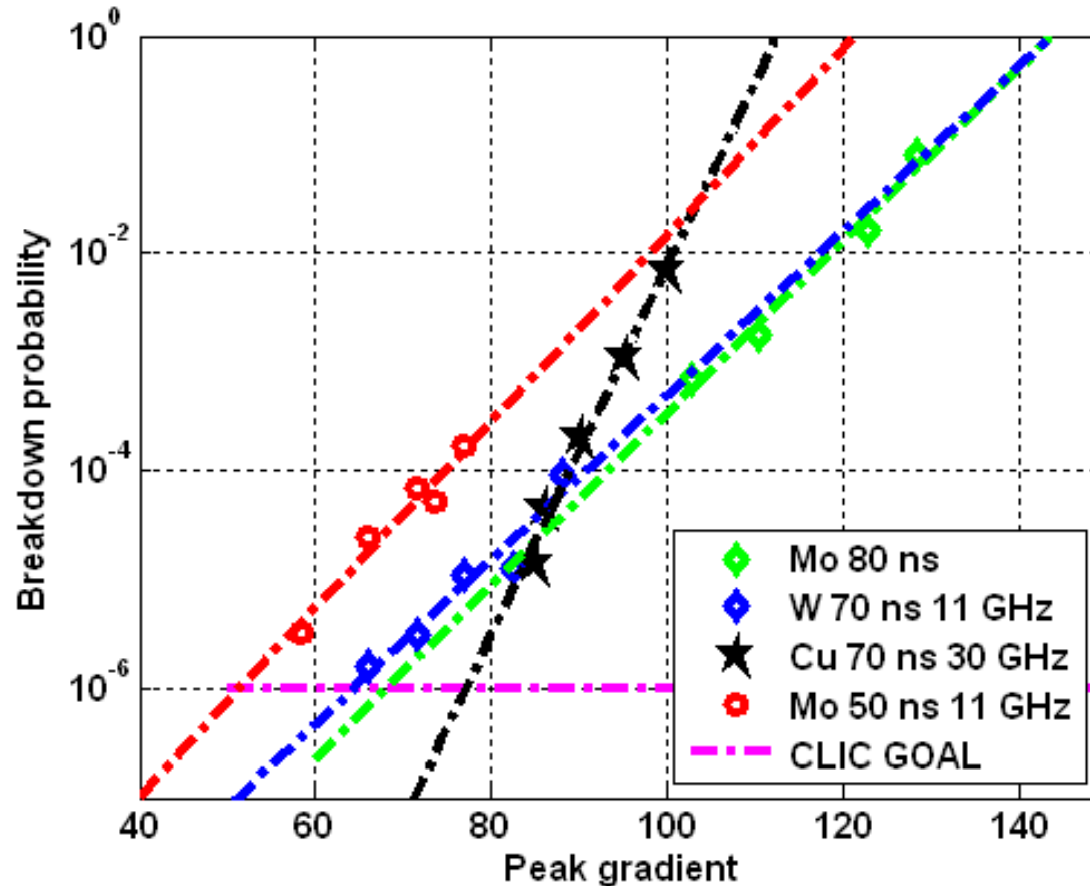

Again frequency scaling not inconsistent
Slope most likely due to iris clamping